

Original Article

## Evaluation of the Effect of Applying Chitosan, Neem, Tulsi, Aloe vera, and Chlorhexidine Solutions on the Shear Bond Strength of Composite to Dentin

Farahnaz Sharafeddin<sup>1</sup>, DMD, MScD; Fatemeh Aghaei<sup>2</sup>, DMD;

<sup>1</sup> Dept. of Operative Dentistry, Biomaterials Research Center, School of Dentistry, Shiraz University of Medical Sciences, Shiraz, Iran.

<sup>2</sup> Postgraduate Student, Dept. of Operative Dentistry, Biomaterials Research Center, School of Dentistry, Shiraz University of Medical Sciences, Shiraz, Iran.

### KEY WORDS

Resin composite;  
Chitosan;  
Neem;  
Tulsi;  
Aloe vera;  
Chlorhexidine;  
Shear bond strength;

Received: 17 May 2023;  
Revised: 9 July 2023;  
Accepted: 19 December 2023;

### Copyright

© Journal of Dentistry, this is an open access article distributed under the terms of the Creative Commons Attribution 4.0 International License, (<http://creativecommons.org/licenses/by/4.0/>) which permits reusers to copy and redistribute the material in any medium or format if the original work is properly cited, and attribution is given to the creator. The license also permits for commercial use.

### ABSTRACT

**Statement of the Problem:** Dentin adhesion is challenging and needs modifications. Newly introduced nature-derived materials may be a useful solution in improving dentin adhesion. The use of natural antimicrobial agents for pretreating prepared dentin surfaces before restoration has become of interest.

**Purpose:** The present study investigated the effect of natural compounds on the shear bond strength (SBS) of resin composite adhesively bonded to dentin.

**Materials and Method:** Sixty extracted human molar teeth were randomly divided into six groups (n= 10); Group I: two-step etch and rinse adhesive system, Adper Single Bond 2 (SB<sub>2</sub>) (experimental control), Group II: 2.5% Chitosan+etch+SB<sub>2</sub>, Group III: 15% Neem (*Azadirachta indica*)+etch+SB<sub>2</sub>, Group IV: 15% Tulsi (*Ocimum sanctum*)+etch+SB<sub>2</sub>, Group V: 2% Aloe vera+etch+SB<sub>2</sub>, and group VI: 2% Chlorhexidine (CHX)+etch+SB<sub>2</sub>. Resin composite (Z350, 3M ESPE USA) was placed over the prepared dentin surfaces and was light cured. Data analysis was performed using One-way ANOVA and post hoc Tukey's test ( $p < 0.05$ ).

**Results:** Neem specimens showed the highest mean SBS, statistically greater than the control ( $p = 0.042$ ). Other experimental groups showed no significant differences in SBS comparison to the control. The mean SBS values of 2.5% Chitosan, 15% Neem, 15% Tulsi, and 2% Aloe vera were significantly higher than 2% CHX ( $p = 0.046$ ,  $p = 0.001$ ,  $p = 0.010$  and  $p = 0.002$  respectively).

**Conclusion:** Dentin pretreatment with Neem may improve the bond strength of a two-step etch and rinse adhesive system. The application of Chitosan, Tulsi, Aloe vera, and CHX did not demonstrate significantly different SBS values from that of the Control, although CHX was lower.

**Corresponding Author:** Aghaei F, Dept. of Operative Dentistry, School of Dentistry, Shiraz University of Medical Sciences, Shiraz, Iran. Tel: +98-7136263193-4 Email: m\_ghaei878@yahoo.com

Cite this article as: Sharafeddin F, Aghaei F. Evaluation of the Effect of Applying Chitosan, Neem, Tulsi, Aloe vera, and Chlorhexidine Solutions on the Shear Bond Strength of Composite to Dentin. J Dent Shiraz Univ Med Sci. December 2024; 25(4): 334-341.

### Introduction

Resin-dentin bond stability is still a major concern in adhesive dentistry [1]. Destruction of the hybrid layer due to collagen fibrils degradation by matrix metalloproteinases (MMPs) and hydrolysis of resin, will compromise the bond strength [2]. Furthermore, the remained bacteria after tooth cavity preparation may deteriorate the microleakage and lead to secondary caries

and pulpal response [1]. Thus in recent years, studies have focused on developing materials with eligible properties such as protease inhibitory effect, antibacterial activities, and remineralizing ability to promote resin-dentin bond longevity [3-6].

Disinfection of the prepared cavity after caries removal can aid in the elimination of microbial remnants [4]. Different materials have been proposed to improve

dentin adhesion like Chlorhexidine digluconate (CHX), Neem (*Azadirachta indica*), and Aloe vera, before acid etching in tooth-colored restorations [4]. They act as antimicrobial agent matrix metalloproteinase (MMP) inhibitors, and so forth. MMPs and cysteine cathepsins, which are found in human dentin, contribute to the degradation of denuded collagen within the hybrid layer [2].

CHX is known as a gold standard cavity disinfectant in restorative dentistry [4, 7] with antimicrobial activity [8], and MMPs inhibitory effect [9]. It has been shown that the degradation of dentin-bonds is reduced with the use of 2% CHX *in vivo* and *in vitro* [10]. However, recently, there has been a growing interest in investigating novel nature-derived materials for adhesive applications [11-12].

Chitosan, Neem, Tulsi (*Ocimum sanctum*), and Aloe vera are some new materials in dentistry that have favorable properties such as biocompatibility, biodegradability, non-toxicity, antibacterial activity, antioxidant properties, and anti-MMPs potential in addition to availability and low cost with no side effects [4-5, 12-13].

Chitosan is a non-toxic biopolymer derived from alkaline deacetylation of chitin [14] and has increased the bond strength in comparison to dentin treated with phosphoric acid or untreated dentin in an *in vitro* study [15].

Neem is an evergreen tree [4] with a long history of being used to treat teeth and gum problems [16]. Aloe vera (*Aloe barbadensis* Miller) is an evergreen plant with antimicrobial activity [4] and anti-MMP properties [5] that may have several potential applications in dentistry [17]. It has been shown that Neem and Aloe vera have improved immediate and delayed SBS [4].

Tulsi is a holy plant of Indian origin [13] with antimicrobial activities against *streptococcus mutans* [18]. It has been shown that Tulsi leaf extract can reverse the negative effect of bleaching on resin-enamel bond strength [19].

Given that there is limited or no data about the effect of these new naturally occurring compounds on resin-dentin bond strength, and considering the need for comparative evaluation of newly introduced materials with each other and with traditional pretreatment materials, the purpose of this study was to investigate and compare the effect of Chitosan, Neem, Tulsi, Aloe vera and CHX on the SBS of resin composite to dentin. The research hypothesis was that pretreatment with these solutions

would improve dentin bond strength and there would be no priority in improved SBS among tested groups.

### Materials and Method

The study was approved by the related Research Ethics Committee (IR.SUMS.DENTAL.REC.1399.024), sixty human third molar teeth with no sign of caries, cracks, defects, and restorations were collected, thoroughly cleaned, and kept in 0.1% thymol suspension at 4°C for 7 days. Afterward, the teeth were mounted in acrylic resin molds (Acropars, Iran) in a manner that the coronal portion of the teeth above the cement-enamel junction was left out of the mold and the occlusal surface was positioned in parallel with acrylic resin.

The occlusal surface of the teeth was sectioned with diamond discs (D and Z, Germany) under copious amounts of water, at a depth of 0.5 mm under the central pit. The sectioned surface was prepared with 600-grit silicon carbide paper (SiC paper, Piramit, Istanbul, Turkey) to obtain a uniform dentin surface. The teeth were randomly divided into six groups (n= 10) according to the pretreatment solutions. The commercial restorative products used in this study are listed in Table 1.

Table 2 shows the description of dentin pretreatment materials of the study. 2.5% chitosan solution was prepared by adding 2.5 gr low molecular weight chitosan powder (Sigma Aldrich, USA) to 0.1% acetic acid. 15% Neem solution was achieved by adding 15 gr neem leaf powder (Indian Neem Tree Company, India) to 100 mL sterile distilled water, and filtration was done after 24 hours first using a silk cloth for coarse particles and followed by a Whatman no. 1 filter paper for fine residue [20]. 15% Tulsi solution (Herbal Heals, India) was prepared in the same manner. 2% Aloe vera solution prepared by adding 20 mg aloe vera powder (Nasim Faraz, Iran) to 100 ml sterile distilled water. As a 2% CHX solution, the Consepsis™ (Ultradent, USA) solution was employed. The methods of dentin treatment are summarized in Table 3 and performed as follows.

**Table 1:** Commercial restorative products of the study

| Material                | Manufacturer             |
|-------------------------|--------------------------|
| Filtek™ Z350 XT         | 3M ESPE, USA             |
| Adper™ Single Bond 2    | 3M ESPE, USA             |
| Scotchbond™ Etchant     | 3M ESPE, USA             |
| Chitosan                | Sigma Aldrich, USA       |
| Self-cure acrylic resin | Acropars, Iran           |
| LED polymerizing unit   | Bluelex, GT 1200, Taiwan |

**Table 2:** Description of dentin pretreatment materials

| Material         | Manufacturer                        | Description  |
|------------------|-------------------------------------|--|
| 2.5% Chitosan    | Sigma Aldrich, USA                  | 2.5 g of low molecular weight Chitosan was dissolved in 100 mL of 1% acetic acid                       |
| 15% Neem         | The Indian Neem Tree Company, India | 15 gr of Neem leaf powder was added to 100 mL sterile distilled water and was filtered after 24 hours  |
| 15% Tulsi        | Herbal Heals, India                 | 15 gr of Tulsi leaf powder was added to 100 mL sterile distilled water and was filtered after 24 hours |
| 2% Aloe vera     | Nasim Faraz, Iran                   | 20 mg Aloe vera powder (Nasim Faraz, Iran) to 100 ml sterile distilled water                           |
| 2% Chlorhexidine | Consepsis, Ultradent, USA           | 2% Chlorhexidine gluconate solution  |

**Group 1:** (Control) 35% phosphoric acid (3M ESPE Scotchbond Etchant, 3M ESPE, USA) was applied on the prepared dentin surface for 15 s and then rinsed for 10 s. After that, the dentin surface was blotted with a cotton pellet to remove excess water. Two coats of Adper Single Bond 2 (SB<sub>2</sub>) (3M ESPE, USA) were applied using a micro brush for 15 s immediately after blotting. Air thinning was then performed for 5 seconds to ensure solvent evaporation.

**Group 2:** Dentin was treated with 2.5% Chitosan solution using gentle rubbing motion of the micro brush for 30, then rinsed for 20 s with water [21] and dried using air spray.

**Group 3:** Dentin was treated with 15% Neem solution using gentle rubbing motion of the micro brush for 30s [4], then rinsed for 20s with water, and dried using air spray.

**Group 4:** Dentin was treated with 15% Tulsi solution using gentle rubbing motion of the micro brush for 30,

**Table 3:** Dentin pretreatments in the study

| Groups  | Treatment  |
|---------|--|
| Group 1 | 35% Phosphoric acid, 15s+SB <sub>2</sub> +resin composite                      |
| Group 2 | 2.5% Chitosan 30s+35% phosphoric acid, 15s+SB <sub>2</sub> + resin composite   |
| Group 3 | 15% Neem 30s+35% phosphoric acid, 15s+SB <sub>2</sub> + resin composite        |
| Group 4 | 15% Tulsi 30s +35% phosphoric acid, 15s + SB <sub>2</sub> + resin composite    |
| Group 5 | 2% Aloe vera 30s+ 35% phosphoric acid, 15s + SB <sub>2</sub> + resin composite |
| Group 6 | 2% CHX 30s + 35% phosphoric acid, 15s + SB <sub>2</sub> + resin composite      |

Adper Single Bond 2 (SB<sub>2</sub>), Chlorhexidine (CHX)

then rinsed for 20 seconds with water, and dried using air spray.


**Group 5:** Dentin was treated with 2% Aloe vera solution using gentle rubbing motion of the micro brush for 30 [5], then rinsed for 20 s with water, and dried using air spray.

**Group 6:** Dentin was treated with an active application of 2% CHX solution (Consepsis, Ultradent, USA) with a micro brush for 30s [4], then rinsed for 20 s with water [22] and dried using air spray.

The treated and washed dentin surfaces were then acid etched (3M ESPE Scotchbond Etchant) followed by the application of dentin bonding agent for groups 2 to 6 as was described in group 1.

The samples were light-cured for 10 s with a light emitting diode (LED) polymerizing unit (Monitex, Bluelex, GT 1200, Taiwan) at the light intensity of 1000 mW/cm<sup>2</sup> and wavelength of 470 nm to cure the adhesive agent and light intensity evaluated by radiometer(DigiRate, Monitex, Taiwan). Resin composite (Filtek Z-250, 3M ESPE, USA) build-up was done by placing an uncured paste of resin composite into a 2 mm thick, 3 mm diameter hole of a clear plastic mold on the prepared dentin surface. The resin composite was then light-cured for 40s. The specimens were kept in distilled water for 24 h at 37°C in an incubator (ES 250 Nuve, Turkey). For shear bond testing, a shear load was to the upper side cylinder wall at the resin-dentin interface using a knife blade edge held in the crosshead of a universal testing machine (Zwick/Roell Z020, Germany) and lowered at a speed of 1.0 mm/minute (Figure 1).

The load observed at fracture (N) was divided by the cross-sectional specimen area to convert results into units of was calculated in MPa.

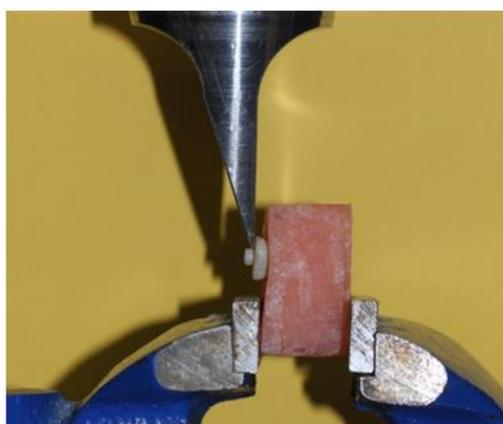

**Figure 1:** A sample in universal testing machine

**Table 4:** Mean shear bond strength (MPa) values±SD in experimental groups

| Groups  | Treatments     | Mean (MPa)±SD |
|---------|----------------|---------------|
| Group 1 | Control        | 12.53±1.866   |
| Group 2 | Chitosan 2.5%  | 13.62±1.816   |
| Group 3 | Neem 15%       | 15.30±2.276   |
| Group 4 | Tulsi 15%      | 14.15±1.500   |
| Group 5 | Aloe vera 0.2% | 14.61±1.514   |
| Group 6 | CHX 2%         | 10.88±2.94    |

Chlorhexidine (CHX)


Statistical analysis was performed using SPSS software, version 21 for Windows (SPSS Inc., Chicago, IL, USA). The Kolmogorov-Smirnov test assessed the normal distribution of the data ( $p < 0.05$ ). One-way ANOVA was implemented for data analysis, and multiple comparisons were done using post hoc Tukey's test ( $p < 0.05$ ).

**Results**

Mean SBS values and standard deviations (MPa) are presented in Table 4.

There was a normal distribution of the data in tested groups. One-way ANOVA showed a significant difference within the mean SBS values of experimental groups ( $p < 0.05$ ). Pairwise means comparison of the experimental groups using Post hoc Tukey's tested for significant.

The highest mean SBS value was observed with 15% Neem solution (Group 3) and the difference was statistically significant compared to the control (Figure 2). Dentin treatment with CHX 2% (Group 6) resulted in the lowest mean SBS value but was not significantly different from the control. Other experimental groups showed

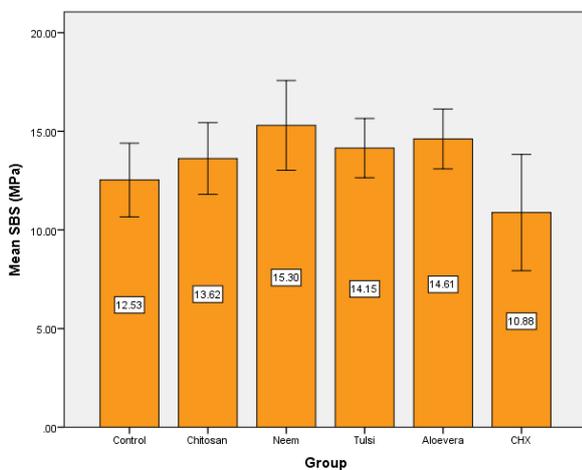

Group 1: Control, Group 2: Chitosan, Group 3: Neem, Group 4: Tulsi, Group 5: Aloe vera, Group 6: Chlorhexidine (CHX)

**Figure 2:** bar plot illustrates mean of the SBS (MPa) in all groups

wed higher mean SBS values than the control without statistically significant differences. Groups 2 (Chitosan 2.5%), 3 (Neem 15%), 4 (Tulsi 15%), and 5 (Aloe vera 0.2%) led to significantly higher mean SBS values than group 6 (CHX 2%) (Table 5).

**Discussion**

Recently there has been a trend to investigate natural biomaterials for dental applications, as the materials derived from nature have favorable properties, such as better biocompatibility, less toxicity, availability, and more affordable costs [12, 23]. In this study, we investigated the SBS of resin composite to dentin with the application of different dentin pretreatment solutions such as Chitosan, Neem, Tulsi, Aloe vera, and CHX with anti-MMPs and antibacterial activity in an attempt to enhance the bond strength of resin composite to dentin. The SBS is widely used as a screen test for new adhesive materials [24], due to requiring minimum equipment, ease of specimen preparation and perform [25].

Different protocols have been reported for steps of application of phosphoric acid, treatment solution, and adhesive systems [25-27]. Chitosan, Neem, Tulsi, Aloe vera, titanium tetrafluoride, and CHX solutions have antimicrobial effects, so reducing microorganisms is an important factor in tooth-colored restorations before acid etching and dentin bonding application [4,13,27]. Therefore, in this *in vitro* study, we assessed new materials using a shear bond test before phosphoric acid gel.

According to the results of the present study, there

**Table 5:** Pairwise comparison of mean shear bond strength (SBS) values between experimental groups using Tukey's test

| Groups (I-J) | Sig    |
|--------------|--------|
| 1-2          | 0.840  |
| 1-3          | 0.042* |
| 1-4          | 0.459  |
| 1-5          | 0.225  |
| 1-6          | 0.475  |
| 2-3          | 0.454  |
| 2-4          | 0.992  |
| 2-5          | 0.887  |
| 2-6          | 0.046* |
| 3-4          | 0.878  |
| 3-5          | 0.954  |
| 3-6          | 0.000* |
| 4-5          | 0.996  |
| 4-6          | 0.010* |
| 5-6          | 0.002* |

\* The mean difference is significant at the 0.05 level

was no significant difference between the mean SBS values of the experimental groups (Group 2,4-6) with the control group (Group 1) except for the samples pretreated with Neem solution (Group 3). So the null hypothesis was partially rejected.

Neem is a medicinal herb with numerous biological effects [28] such as antibacterial activity, especially against *Streptococcus mutans* and *Lactobacillus sp*, anti-MMPs activity against MMP-2 and MMP-9, and the ability to remove the smear layer [4, 28-30]. In the present study, dentin pretreatment with Neem solution resulted in the highest mean SBS values amongst the tested groups and the difference was statistically significant compared to the control. Our finding is in agreement with the results of Shivika Goel *et al.* [4] study that revealed the application of Neem enhanced immediate and delayed bond strengths in comparison to the control. The positive effect of Neem on resin-dentin bond strength in our study may be attributed to its smear layer removal effect. On the other hand, we actively applied Neem solution on dentin, which may have enhanced the interaction of the material with the underlying dentin and helped in better smear layer removal resulting in higher bond strength to dentin.

One of the tested materials of the present study was Tulsi, which is considered a medicinal herb with potential promising applications in dentistry. To date, our study is the first research that evaluated the effect of Tulsi on resin-dentin bond strength. In the present study, Tulsi showed higher SBS than the control group but the difference was not significant. This finding may be due to its poor smear layer removal efficacy [28]. It should be noted that the most active chemical constituent of Tulsi is eugenol [31]. However, despite the known inhibitory effect of eugenol on the polymerization of methacrylate monomers and its incompatibility with the resin restorative systems [32], the bond strength was not compromised using Tulsi in the present study. It can be ascribed to the short exposure time of dentin to the eugenol-containing solution. Furthermore, 15% Tulsi solution was used which is low concentration, and dentin was not exposed to high amounts of eugenol. In addition, a two-step etch and rinse adhesive system was used, and the acid etch application after treatment of dentin with Tulsi may have removed eugenol and prevented interaction between eugenol and bonding agent.

Since there is no similar study about the effect of Tulsi on the bond strength, it seems that the application of Tulsi as a cavity disinfectant may not compromise the bond strength of resin composite to dentin.

Aloe vera is a medicinal plant with desirable properties such as antibacterial, antioxidant, and anti-MMPs activity in addition to availability and biocompatibility [17, 33-34]. In the present study, no significant increase in SBS was obtained with Aloe vera in comparison to the control. This finding is in contrast to the results of two recent studies conducted by Shivika Goel *et al.* [4] and Dakshina Joy Sinha *et al.* [5] that indicated Aloe vera improved the SBS using a two-step etch and rinse adhesive. Since the two studies mentioned above used the same adhesive system, and similar concentration and application time of Aloe vera to our study, the different yielded outcomes might be contributed to the step of application of the Aloe vera. They applied aloe vera after acid etching, while we applied Aloe vera before acid etching. Therefore, it might have been removed by etching and was not allowed to interact with dentin. Furthermore, Keerthana T *et al.* [35] showed that the application of aloe vera gel before a self-etch adhesive significantly reduces the SBS. This may be due to the application of Aloe vera in a high-viscosity gel form without following rinsing, which may have reduced contact area between the dentin surface and self-etch adhesive and inhibited the penetration of acidic monomers to the dentin surface. Consequently, the hybrid layer could not be formed properly resulting in decreased bond strength.

Chitosan is a natural biopolymer that has potentially beneficial properties in adhesive dentistry such as biocompatibility, a wide range of antibacterial activity, and the ability to improve the resistance of dentinal surface to degradation by collagenase [36-37]. Chitosan can remove or modify the smear layer depending on its concentration [3]. It also may play a role in opening interfibrillar spaces and may have a significant effect on resin permeation and the creation of a hybrid layer [21].

According to our findings, application of 2.5% Chitosan solution before acid etching of dentin resulted in higher mean SBS values without statistically significant difference to the control group. Similar to our finding, a study by Vasei *et al.* [14] showed that after 24 hours of water storage, Chitosan did not significantly affect the

SBS. Obtaining no improvement in SBS may be due to following phosphoric acid application, which is strong enough to eliminate the smear layer. It can be hypothesized that the smear layer removal ability of 2.5% chitosan has no synergistic effect with phosphoric acid thus; it could not enhance the bond strength.

On the contrary, Lukram Nivedita *et al.* [21] showed that the application of Chitosan improved the SBS to dentin as compared to the control. It may be attributed to the step of Chitosan application, as we applied Chitosan before acid etching, but they applied Chitosan after acid etching of dentin. On the other hand, it has been shown that when the concentration of Chitosan increases, the bond strength value decreases [3]. In the study mentioned above, 1.2% Chitosan solution was used, while in the present study, we used 2.5% Chitosan solution. Therefore, different concentrations may have resulted in different outcomes.

In the current study, CHX showed lower SBS but was not significantly different from the control. This finding is in line with the outcomes of previous studies that showed CHX did not compromise the resin-dentin bond strength [10, 38-39]. Contrary to our results, DW Elkassas *et al.* [40] found that pretreatment with CHX significantly reduced immediate bond strength when applied with a two-step etch and rinse adhesive. This contrast could be due to the different application times, as in their study CHX was applied for 60s, while we used CHX for 30s. It has been shown that CHX can stabilize the smear layer making it resistant to removal by etchant [38]. It seems that the stabilizing effect of CHX on the smear layer may compromise the bond strength in prolonged application of CHX.

In the present study, CHX showed significantly lower bond strength compared to other experimental materials. The superiority of Chitosan, Neem, Tulsi, and Aloe vera to CHX in terms of bond strength suggests that these materials may be good alternatives to CHX as a cavity disinfectant. However, more research is needed to validate this laboratory finding before the presentation of these materials for widespread use in adhesive dentistry.

This *in vitro* study was performed in laboratory conditions, which might not simulate the oral environment variables completely. Thus, future *in vivo* studies are suggested before the generalization of the outcomes to

clinical applications. In addition, further studies are recommended to investigate the long-term effect of tested materials on the SBS, other application methods, and other adhesive systems.

### Conclusion

Based upon the limitations imposed by the methods of the current study, it can be concluded that dentin pretreatment with Neem may enhance bond strength of resin composite to dentin. Dentin pretreatment with Chitosan, Tulsi, Aloe vera, and CHX did not compromise resin-dentin bond strength. Higher bond strength was obtained with Chitosan, Neem, Tulsi, and Aloe vera in comparison to CHX. Hence, these materials might be good alternatives to CHX as a cavity disinfectant.

### Acknowledgments

The authors thank the Vice-Chancellery of Shiraz University of Medical Science for supporting this research (Grant #21156). This manuscript was based on the thesis by Dr. Fatemeh Aghaei for a postgraduate specialty course in operative dentistry (Code: 1398-01-03-21156). The authors also thank Dr. Vossoughi from the Dental Research Development Center for the statistical analysis and Mrs. Bagheri from the Biomaterials Research Center for experimental tests.

### Conflict of Interest

The authors have declared that no conflict of interest exists.

### References

- [1] Reis A, Loguercio AD, Chibinski AC. Some Myths in Dentin Bonding: An Evidence-Based Perspective. *J Dent Res.* 2023; 102: 376-382.
- [2] Albuquerque N, Neri JR, Lemos M, Yamauti M, de Sousa F, Santiago SL. Effect of polymeric microparticles loaded with catechin on the physicochemical properties of an adhesive system. *Oper Dent.* 2019; 44: E202-E211.
- [3] Mohamed AM, Nabih SM, Wakwak MA. Effect of chitosan nanoparticles on micro tensile bond strength of resin composite to dentin: an *in vitro* study. *Braz Dent Sci.* 2020; 23: 10.
- [4] Goel S, Sinha DJ, Singh UP, Ahuja U, Haider N, Sharma N. Comparative evaluation of the effect of chlorhexidine, *Azadirachta indica* (neem), and *Aloe barbadensis miller*

- (Aloe vera) on resin-dentin bond stabilization using shear bond testing: an in vitro study. *J Conserv Dent.* 2019; 22: 300.
- [5] Sinha DJ, Jandial UA, Jaiswal N, Singh UP, Goel S, Singh O. Comparative evaluation of the effect of different disinfecting agents on bond strength of composite resin to dentin using two-step self-etch and etch and rinse bonding systems: An in vitro study. *J Conserv Dent.* 2018; 21: 424.
- [6] Gajjela RS, Satish RK, Sajjan GS, Varma KM, Rambabu T, Lakshmi BV. Comparative evaluation of chlorhexidine, grape seed extract, riboflavin/chitosan modification on micro tensile bond strength of composite resin to dentin after polymerase chain reaction thermocycling: An in vitro study. *J Conserv Dent.* 2017; 20: 120.
- [7] Mohammed Hassan A, Ali Goda A, Baroudi K. The effect of different disinfecting agents on bond strength of resin composites. *Int J Dent.* 2014; 2014: 231235.
- [8] Sharafeddin F, Farhadpour H. Evaluation of shear bond strength of total-and self-etching adhesive systems after application of chlorhexidine to dentin contaminated with a hemostatic agent. *J Dent (Shiraz).* 2015; 16: 175.
- [9] Gendron R, Grenier D, Sorsa T, Mayrand D. Inhibition of the activities of matrix metalloproteinases 2, 8 and 9 by chlorhexidine. *Clin Diagn Lab Immunol.* 1999; 6: 437-439.
- [10] Sabatini C. Effect of a chlorhexidine-containing adhesive on dentin bond strength stability. *Oper Dent.* 2013; 38: 609-617.
- [11] Zhang Z, Yu J, Yao C, Yang H, Huang C. New perspective to improve dentin-adhesive interface stability by using dimethyl sulfoxide wet-bonding and epigallocatechin-3-gallate. *Dent Mater.* 2020; 36: 1452-1463.
- [12] Kmiec M, Pighinelli L, Tedesco M, Silva M, Reis V. Chitosan-properties and applications in dentistry. *Adv Tissue Eng Regen Med Open Access.* 2017; 2: 00035.
- [13] Chandrappa PM, Dupper A, Tripathi P, Arroju R, Sharma P, Sulochana K. Antimicrobial activity of herbal medicines (tulsi extract, neem extract) and chlorhexidine against *Enterococcus faecalis* in Endodontics: An in vitro study. *J Int Soc Prev Community Dent.* 2015; 5: 89-92.
- [14] Vasei F, Sharafeddin F. Effect of chitosan treatment on shear bond strength of composite to deep dentin using self-etch and total-etch adhesive systems. *Braz Dent Sci.* 2021; 24: 1-9.
- [15] Perchyonok T, Grobler SR, Zhang S, Olivier A, Oberholzer T. Insights into chitosan hydrogels on dentine bond strength and cytotoxicity. *Open J Stomatol.* 2013; 3: 75-82.
- [16] Arora T, Kang RS, Mann JS, Khurana NS, Aggarwal R, Walia G. Antimicrobial activity of herbal extracts against recalcitrant endodontic pathogens: An original in vitro study. *Saint Int Dent J.* 2015; 1: 28-32.
- [17] Mangaiyarkarasi S, Manigandan T, Elumalai M, Cholan PK, Kaur RP. Benefits of Aloe vera in dentistry. *J Pharm Bioall Sci.* 2015; 7: 255-259.
- [18] Chaurasia A, Tulsi A. Promising herb in dentistry. *Oral Surg Oral Med Oral Pathol Oral Radiol.* 2015; 1: 21-23.
- [19] Rai AVNB. The comparative evaluation of the effect of three natural antioxidants on the bond strength of composite resin to bleached enamel- an in vitro study. *Int J Curr Res.* 2020; 12: 9900-9906.
- [20] Siddique R, Sureshbabu NM, Somasundaram J, Jacob B, Selvam D. Qualitative and quantitative analysis of precipitate formation following interaction of chlorhexidine with sodium hypochlorite, neem and tulsi. *J Conserv Dent.* 2019; 22: 40.
- [21] Nivedita L, Prakash V, Mitthra S, Mary NSGP, Venkatesh A, Subbiya A. Evaluation of the effect of collagen stabilizing agents like chitosan and proanthocyanidin on the shear bond strength to dentin and microleakage of resin composite at enamel and cemental walls: An in vitro study. *J Conserv Dent.* 2019; 22: 483.
- [22] Saffarpour A, Saffarpour A, Kharazifard MJ, Rad AE. Effect of chlorhexidine application protocol on the durability of marginal seal of class v restorations. *J Dent (Tehran).* 2016; 13: 231.
- [23] Dick TNA, Marques LC, Lopes AdAL, Candreva MS, Santos LR, Picciani BLS. Phytotherapy in dentistry: a literature review based on clinical data. *European J Med Plants.* 2020; 31: 1-13.
- [24] El Mourad AM. Assessment of bonding effectiveness of adhesive materials to tooth structure using bond strength test methods: a review of literature. *Open Dent J.* 2018; 12: 664.
- [25] Sharafeddin F, Safari M. Effect of papain and bromelain enzymes on shear bond strength of composite to superficial dentin in different adhesive systems. *J Contemp Dent Pract.* 2019; 20: 1077-1081.
- [26] Sharafeddin F, Haghbin N. Comparison of bromelain enzyme, sodium hypochlorite and titanium tetrafluoride on shear bond strength of restorative composite to dentin:

- an in vitro study. *J Dent (Shiraz)*. 2019; 20: 264- 270.
- [27] Devabhaktuni S, Manjunath MK. Effect of 4% titanium tetrafluoride application on shear bond strength of composite resin: An in vitro study. *J Conserv Dent*. 2011; 14: 43-45.
- [28] Kumar A, Sarthaj S, Antony M. Comparative Evaluation of Antibacterial and Smear Layer Removal Efficacy of Two Different Herbal Irrigants: An In Vitro Study. *IHRJ*. 2018; 1: 350-354.
- [29] Lakshmi T, Krishnan V, Rajendran R, Madhusudhanan N. *Azadirachta indica*: A herbal panacea in dentistry: An update. *Pharmacogn Rev*. 2015; 9: 41.
- [30] Kaushik A, Tanwar R, Kaushik M. Ethnomedicine: Applications of Neem (*Azadirachta indica*) in dentistry. *Dental Hypotheses*. 2012; 3: 112.
- [31] Lakshmi T. *Ocimum Sanctum* in Dental Care-A Mini Review. *Res J Pharm Technol*. 2014; 7: 101-103.
- [32] Lopes MB, Felizardo KR, Kaneshima RH, Guiraldo SB, Guiraldo RD, Júnior AG. Influence of eugenol-based materials and cleaning procedures previously to resin composite restoration on microleakage after 1-year storage. *Appl Adhes Sci*. 2016; 4: 15.
- [33] Sharafeddin F, Farshad F. The effect of aloe vera, pomegranate peel, grape seed extract, green tea, and sodium ascorbate as antioxidants on the shear bond strength of composite resin to home-bleached enamel. *J Dent (Shiraz)*. 2015; 16: 296.
- [34] Kudalkar MD, Nayak A, Bhat KS, Nayak RN. Effect of *Azadirachta indica* (Neem) and Aloe vera as compared to subantimicrobial dose doxycycline on matrix metalloproteinases (MMP)-2 and MMP-9: An in vitro study. *Ayu*. 2014; 35: 85-89.
- [35] Keerthana TSR. Influence of various cavity disinfectants on bond strength of self etch adhesives: an in vitro study. *Int J Pharm Sci Res*. 2020; 12: 1873-1880.
- [36] Kishen A, Shrestha S, Shrestha A, Cheng C, Goh C. Characterizing the collagen stabilizing effect of cross-linked chitosan nanoparticles against collagenase degradation. *Dent Mater*. 2016; 32: 968-977.
- [37] Zidan A. Effect of chitosan on resin-dentin interface durability: A 2-year in-vitro study. *Egypt Dent J*. 2019; 65: 2955-2965.
- [38] Hajizadeh H, Bojarpour M, Borouziniat A, Namdar F. The effect of chlorhexidine application on the microtensile bond strength and durability of a total-etch adhesive. *European J Gen Dent*. 2020; 9: 17.
- [39] Dalli M, Ercan E, Zorba YO, İnce B, Şahbaz C, Bahşi E, et al. Effect of 1% chlorhexidine gel on the bonding strength to dentin. *J Dent Sci*. 2010; 5: 8-13.
- [40] Elkassas DW, Fawzi EM, El Zohairy A. The effect of cavity disinfectants on the micro-shear bond strength of dentin adhesives. *Eur J Dent*. 2014; 8: 184.