

Original Article

Efficacy of Remineralizing Agents for Prevention of Microhardness Reduction and Change in Mineral Content of Enamel in Anterior Primary Teeth after Exposure to Iron Drop

Aneseh Sadat Tabatabaei Rad¹, DMD Student; Sara Tavassoli-Hojjati², MScD; Reyhane Sadat Hoda¹, DMD Student; Saba Aghaei², MScD;

¹ General Dentist, School of Dentistry, Islamic Azad University of Tehran, Tehran, Iran.

² Dept. of Pediatric, Faculty of Dentistry, Tehran Medical Sciences, Islamic Azad University, Tehran, Iran.

KEY WORDS

Dental Enamel;
Hardness;
Iron Compounds;
Scanning Electron Microscopy;
Tooth Remineralization;

Received: 6 January 2024;

Revised: 10 March 2024;

Accepted: 20 July 2024;

Copyright

© Journal of Dentistry, this is an open access article distributed under the terms of the Creative Commons Attribution 4.0 International License, (<http://creativecommons.org/licenses/by/4.0/>) which permits reusers to copy and redistribute the material in any medium or format if the original work is properly cited, and attribution is given to the creator. The license also permits for commercial use.

ABSTRACT

Background: Some alterations in the enamel structure of primary teeth have been reported following iron drop consumption. The efficacy of different remineralizing agents for this problem is still challenging.

Purpose: This study aimed to assess the efficacy of remineralizing agents for prevention of microhardness reduction and change in primary enamel mineral content after exposure to iron drop.

Materials and Method: In this experimental study, 36 sound primary anterior teeth were assigned to four groups of control, casein phosphopeptide amorphous calcium phosphate (CPP-ACP), fluoride varnish (FV), and CPP-ACP+FV (MI varnish). The baseline microhardness of the teeth was first measured by Vickers hardness tester using 50 g load for 10 seconds. Next, the microhardness was measured after remineralizing agents were applied on the specimens. After the application of iron drop for 5 minutes, and pH cycling for 10 days, the final microhardness of specimens was registered. Specimens were also subjected to energy dispersive X-ray spectroscopy (EDS) in the control group, after remineralization and after the application of iron drop. Data were analyzed by one-way ANOVA, Tukey's test, and Tamhane's test.

Results: The final microhardness was significantly higher in all remineralized groups compared to the control group (p Value= 0.003). The final microhardness was significantly higher in MI varnish compared to FV ($p= 0.027$), CPP-ACP ($p= 0.03$), and control ($p< 0.0001$) groups. According to EDS, calcium (Ca) and ferric (Fe) content were significantly different between the remineralizing groups and control groups in the final step ($p< 0.00001$).

Conclusion: Application of CPP-ACP, FV, and MI varnish prior to iron drop exposure can improve microhardness. MI varnish had significantly higher efficacy for this purpose than the other two remineralizing agents.

Corresponding Author: Aghaei S, Dept. of Pediatric, Faculty of Dentistry, Tehran Medical Sciences, Islamic Azad University, Tehran, Iran. Tel: +98-9121976173 Fax: +98-2122564571 Email: Saba.agherae@gmail.com

Cite this article as: Tabatabaei Rad AS, Tavassoli-Hojjati S Hoda RS, Aghaei S. Efficacy of Remineralizing Agents for Prevention of Microhardness Reduction and Change in Mineral Content of Enamel in Anterior Primary Teeth after Exposure to Iron Drop. *J Dent Shiraz Univ Med Sci.* June 2025; 26(2): 112-120.

Introduction

The prevalence of iron deficiency was 18% to 38% in Iranian children under 5 years of age in 2004 [1-5]. In addition, the adverse effects of iron deficiency anemia on young children often continue over years, and decrease their cognitive function, and physical and behav-

ioral performance and adverse effect on different part of body such as central nervous system, gastrointestinal, and immunity [6]. Iron drops are prescribed after 6th month to 2 years to prevent iron deficiency [1, 6]. The majority of iron supplements contain citric acid to improve their flavor and taste; however, citric acid de-

creases the pH and increases the solubility of tooth structure [5], resulting in dental erosion [7] and microhardness reduction [1, 3]. In addition, increased enamel surface roughness results in dark discoloration and development of dental caries [1-4, 8].

It has been demonstrated that casein phosphopeptide amorphous calcium phosphate (CPP-ACP) can enhance remineralization and could prevent dental caries [9]. CPP-ACP is a bioactive agent derived from milk protein. Casein phosphopeptide (CPP) binds to dental plaque, soft tissue, and tooth and provides a supersaturated state of minerals in the enamel by stabilization and localization of amorphous calcium phosphate (ACP) [10]. As a result, mineral loss due to acid attacks would be reduced [11]. The cariostatic and remineralizing properties of fluoride have been well documented [11]. The synergistic effects of CPP-ACP and fluoride for prevention of demineralization have been previously reported as well [12-14]. A previous study showed that simultaneous application of CPP-ACP and fluoride varnish (FV) for the prevention of enamel demineralization was more effective than monotherapy with each of them alone [13]. Another study revealed that MI varnish containing CPP-ACP and fluoride significantly decreased demineralization compared with each of them alone [15]. Nonetheless, the efficacy of these bioactive remineralizing agents in the prevention of primary enamel microhardness reduction due to exposure to iron drop has not been previously investigated. Thus, this study aimed to assess the efficacy of remineralizing agents for prevention of microhardness reduction and change in mineral content of enamel in anterior primary teeth following exposure to iron drop.

Materials and Method

In this experimental study (ethical approval code: IR.IAU.DENTAL.REC.1400.043), the minimum sample size was calculated to be 9 in each of the four groups according to a study by Mohammed *et al.* [16] assuming $\alpha=0.05$, $\beta=0.2$, mean standard deviation of 1.5, and effect size of 0.62 using one-way ANOVA power analysis feature of SPSS 26.

A total of 36 sound primary maxillary anterior teeth with no caries, cracks, fracture, restoration, or hypoplasia in their crowns were included in this study (with satisfaction of parents) [1-3, 17-19]. The teeth were

inspected under a stereomicroscope (LV-TV, Nikon, Japan) at 40× magnification to ensure absence of cracks. The maximum time interval between tooth extraction and the experiment was 3 months [1]. All teeth were immersed in 0.5% chloramine T solution for one week and stored in distilled water at 4°C until the experiment [20]. The enamel microhardness of primary teeth was measured before and after exposure to iron drop and also before the application of remineralizing agents by a Vickers hardness tester (Wilson Hardness Tukon 1202, Buehler, USA) [19, 21]. The specimens underwent the following eight steps as follows.

Specimen preparation

The entire crown surfaces of all 27 primary maxillary anterior teeth were coated with nail varnish (Natural Purl, Iran) except for a 4×4mm window in the labial surface [21].

Baseline measurement of microhardness

The teeth were mounted in light-cure acrylic resin (Megadent, Megatray, Germany) such that their lingual surface was mounted in acrylic resin while their labial surface was exposed (facing out) [18]. To obtain a smooth enamel surface for indentation, the labial surface was polished with 800, 1000, and 2000-grit silicon carbide abrasive papers (Smirdenx, Greece) under running water [3, 5, 21-22]. Each abrasive paper was used with 90-degree rotation compared with the previous abrasive paper for each surface to obtain a smooth surface for indentation and measurement of microhardness. The microhardness of specimens was measured by a Vickers hardness tester [1, 18, 22]. The labial surface of the teeth was assessed, and the indenter applied 50 g load for 10 seconds to create a square-shaped indentation [18]. The Vickers hardness number (VHN) of each specimen was measured at three points as such, and the mean of the three values was recorded as the VHN of the respective specimen [1, 18]. Teeth with a VHN value of 239 to 478 were selected for this study [18]. The teeth were then immersed in distilled water at room temperature [3, 20, 22].

Remineralization

The teeth were randomly assigned to three groups by simple randomization using a computer-generated table of random numbers, such that 9 teeth were assigned to each group of CPP-ACP, FV, and MI varnish (a combination of CPP-ACP and FV).

In each group, CPP-ACP (Tooth Mousse/GC, USA), FV (Flouro Dose/centric, USA), and MI varnish (GC, USA) were applied on the window created on the buccal surface for 4 hours. Next, they were removed by a cotton swab dipped in acetone, and the tooth surface was rinsed with distilled water [23].

After the application of remineralizing agents, the teeth were immersed in artificial saliva with the composition of 1.5 mM CaCl₂, 0.9 mM NaH₂PO₄, and 0.15 M KCl with a pH of 7 for 24 hours [21]. Next, each tooth was split in half labiolingually along the longitudinal axis and at the center of the created window using a diamond disc (Prodont Holliger, France) (Figures 1-2). One-half of each tooth underwent the next steps and the other half was used for assessment of mineral content by energy dispersive X-ray spectroscopy (EDS).

Measurement of secondary microhardness

Tooth halves subjected to remineralizing agents were removed from the artificial saliva and rinsed with distilled water [3, 16, 22]. Their microhardness was then measured again blindly by a Vickers hardness tester.

Exposure to iron drop

Acetone was used to remove nail varnish from the tooth halves. They were then exposed to iron drop (Irofant ferrous sulfate, Kharazmi, Iran) for 5 minutes at 37°C in a shaker incubator (Shin Saeng, Korea) [1, 3, 18, 22, 24]. This iron drop contains 125.1mg ferrous sulfate heptahydrate per each 1 mL (25 drops) and 25 mg sodium saccharine (as sweetener) [3, 22].

The pH cycling

Measurement of final microhardness

Measurement of mineral content

Statistical analysis

Results



Figure 1: Samples halves



Figure 2: Another aspect of sample halves

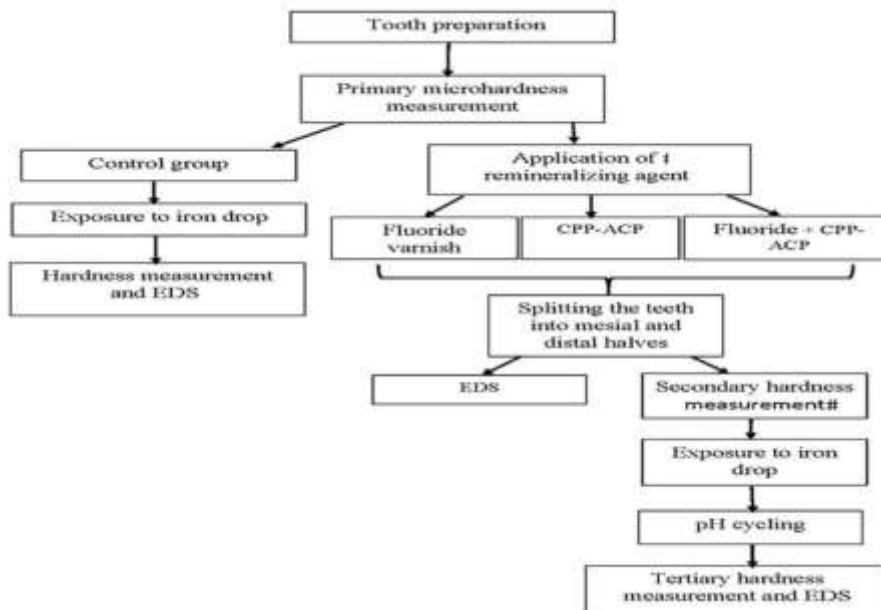


Figure 3: Study design flow diagram

the third step (after exposure to iron drop) decreased by 52% in FV, 51% in CPP-ACP, and 48% in MI varnish group, compared with the second step. This reduction was 63% in the control group that was only exposed to iron drop and did not receive remineralizing agents.

One-way ANOVA showed a significant difference in the amount of Ca ($p= 0.009$) and Fe ($p< 0.0001$) ions on the external tooth surface in different groups. The highest calcium content was noted in CPP-ACP group and the lowest in the control group. Also, the highest iron content was found in the control group and the lowest in MI varnish group. Considering the variance and data distribution in each group, pairwise comparisons of the groups were conducted by the Tukey's test

for the calcium content and by the Tamhane's test for the iron content. The Tukey's test showed that the difference in calcium content was significant between the control and MI varnish ($p= 0.030$), and control and CPP-ACP ($p= 0.009$) groups. The Tamhane's test revealed significant differences between the control group with CPP-ACP ($p= 0.007$), FV ($p= 0.007$), and MI varnish ($p= 0.004$) groups regarding the iron content. The elemental content of the two halves of each tooth (the half subjected to remineralizing agents and iron, and the other half subjected to remineralizing agents) was compared within each group by paired sample t-test. In total, the iron content was higher and the calcium content was lower in tooth halves, subjected to iron drop and remin

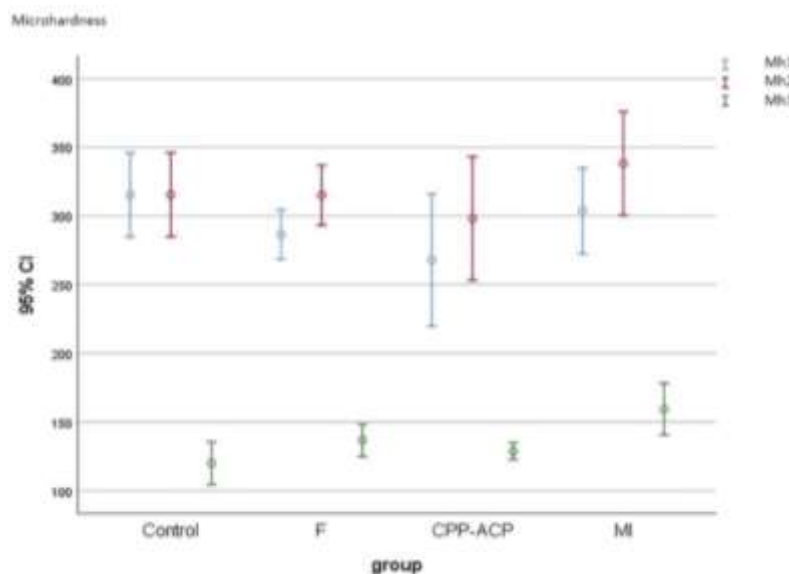


Figure 4: Microhardness of the groups at three steps

Table 1: Mean Microhardness (VHN) and mineral content of the groups

Tests	Mean± SD Microhardness (Kgf/mm ²)			p Value Multiple Comparisons Tukey HSD	Mean± SD Mineral content (wt%)								p Value Paired Samples Test
	Mh1 ^a	Mh2 ^b	Mh3 ^c		Ca	CaH	P	PH	F	FH	Fe	FeH	
Control (iron)	315.4000 ± 39.80710	-	119.8667 ± 20.27042		65.3433 ± 2.44856	-	28.9078 ± 3.19174	-	0.3144 ± 0.55935	-	5.1522 ± 1.95029	-	
FV	286.4222 ± 23.41654	315.2333 ± 28.39820	136.5889 ± 15.34784	Mh1-Mh2: <0.0001* Mh1- Mh3: <0.0001* Mh2- Mh3: <0.0001*	67.3267 ± 1.95630	69.7011 ± 1.09235	30.3856 ± 1.97467	30.0356 ± 1.01214	0.2567 ± 0.37829	0.1511 ± 0.21292	2.0311 ± 0.49245	0.1122 ± 0.11454	Ca-CaH#: 0.007* P-PH#: 0.627 F-FH#: 0.467 Fe-FeH#: <0.0001*
MI varnish	303.6556 ± 40.63423	338.2444 ± 49.08457	159.2444 ± 24.44673	Mh1-Mh2: <0.0001* Mh1- Mh3: <0.0001* Mh2- Mh3: <0.0001*	67.9722 ± 1.68534	72.1456 ± 2.29956	29.7989 ± 1.60973	27.4911 ± 2.14565	0.3867 ± 0.38846	0.2000 ± 0.30871	1.7422 ± 0.34734	0.1633 ± 0.13398	Ca-CaH: 0.002* P-PH: 0.032* F-FH: 0.098 Fe-FeH: <0.0001*
CPP- ACP	267.9111 ± 62.64398	298.1222 ± 58.60955	128.6222 ± 8.09966	Mh1-Mh2: <0.0001* Mh1- Mh3: <0.0001* Mh2- Mh3: <0.0001*	68.3944 ± 1.33720	70.2267 ± 0.86324	29.5100 ± 1.39556	29.5100 ± 0.99911	0.1144 ± 0.12885	0.1611 ± 0.32402	1.9811 ± 0.41664	0.1033 ± 0.12217	Ca-CaH: 0.013* P-PH: >0.999 F-FH: 0.716 Fe-FeH: <0.0001*
p value	0.133	0.331	<0.0001*		0.009*	-	0.541	-	0.520	-	<0.0001*	-	

- Mineral content was measured after the application of the iron drop in the control group and after the application of remineralizing agents+iron drop in the study groups as remineralizing agents were not applied in the control group, Mhs2 was not measured in this group.

*: significant

a: Mh1: First microhardness

b: Mh2: Microhardness after consuming remineralizing agent

c: Mh3: Microhardness after using iron drop

#: CaH/FeH/PH/FH: Ca, Fe, P, F content in dental halves that were only under the effect of remineralizing agent

eralizing agents, compared with other halves, subjected to remineralizing agents alone (Table 1 and Figure 5).

Discussion

As consuming iron drop supplements leads to demineralization and reduction of primary enamel microhardness among children [11], this study aimed to assess the efficacy of CPP-ACP, FV, and MI varnish for the prevention of microhardness reduction and mineral content change of enamel in anterior primary teeth following exposure to iron drop.

The present study found no significant difference in enhancement of microhardness among the tested remineralizing agents ($p > 0.05$). MI varnish and CPP-ACP create a super-saturated state of calcium and phosphorus at the tooth surface, which enhances enamel remineralization and limits demineralization and mineral loss in the process of caries development [13]. In addition, FV

results in formation of calcium fluoride (CaF₂) deposits and increases enamel resistance, enhances remineralization, and subsequently improves the microhardness of the teeth [25].

Our results revealed that iron drop significantly decreased the surface microhardness in all study groups, which was in accordance with the studies of Tabari *et al.* [1], Mehran *et al.* [3], and Pasdar *et al.* [18]. Also, Abbasi *et al.* [26] evaluated the effect of iron drop and multivitamins on microhardness of primary teeth and found that Kharazmi iron drop caused 43.47% reduction in primary enamel microhardness. Iron drop decreases the microhardness by two mechanisms. It contains citric acid with a pH of 2.54 to 4.68 which is lower than 5.5, and increases the solubility and dissolution of hydroxyapatite, and development of dental erosion [26]. Acidic compounds are added to medications and supplements as a buffer to preserve chemical stability, control cohesi-

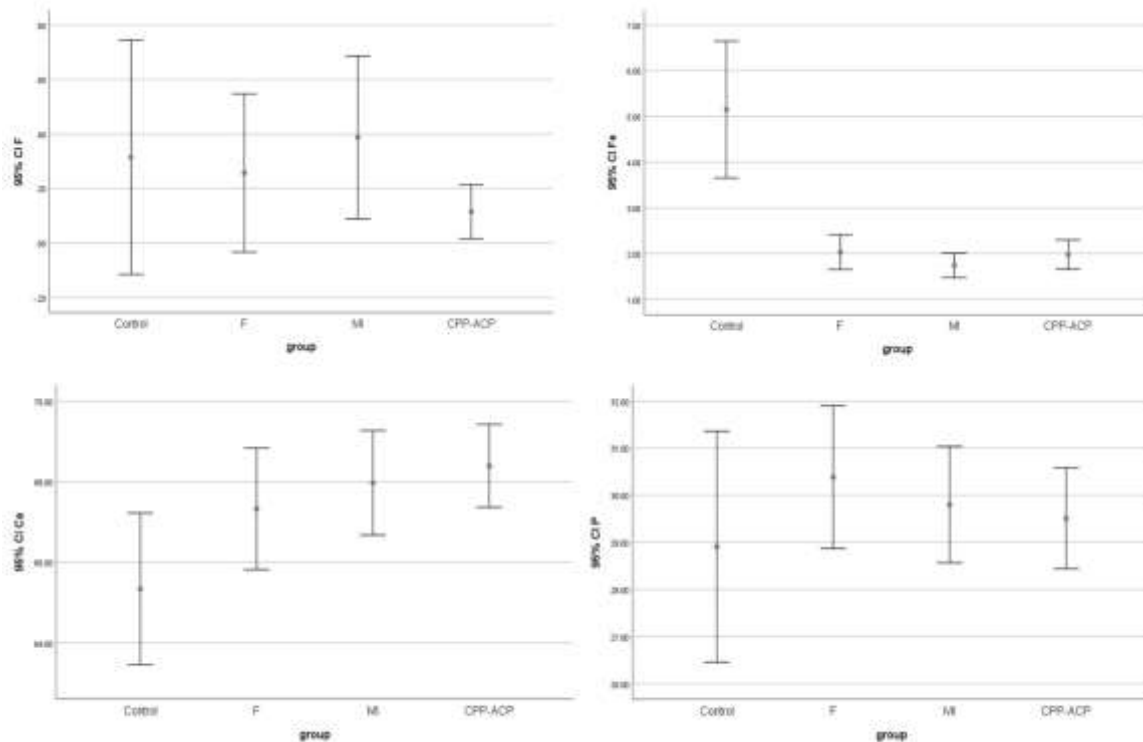


Figure 5: Ca, F, P and Fe contents of the study groups as shown by energy-dispersive X-ray spectroscopy (EDS)

on, and enhance physiological compatibility, solubility, and taste, and subsequently improve their acceptance by patients [27-28]. Moreover, when enamel is incubated with iron salts, ferric sulfate deposits will form on the enamel surface due to interaction of iron ions with insoluble phosphates. This composition has a weaker structure than calcium phosphate and decreases the microhardness of the teeth [29-31]. Since primary enamel is less mineralized than permanent enamel, it is more susceptible to dental erosion and discoloration following the consumption of compounds with a low pH [32].

The present study indicated that the application of remineralizing agents on primary teeth prevented the reduction in microhardness following exposure to iron drop to some extent. MI varnish was significantly more effective than CPP-ACP and FV for this purpose ($p < 0.0001$). Moreover, in some other studies comparing the efficacy of these products in prevention of erosion, the demineralization prevention potential of MI varnish was higher than that of FV and CPP-ACP [13, 15]. Application of CPP-ACP along with fluoride has a synergistic effect on enamel remineralization and formation of stabilized amorphous calcium phosphate fluoride, which results in increased participation of fluoride ions and increased concentration of available calcium and phos-

phate ions [13]. To date, only one study has been conducted on prevention of adverse effects of iron drops. Tabari *et al.* [1] used nano-hydroxyapatite and chitosan remineralizing agents prior to exposure of teeth to iron drops. They reported the minimal efficacy of this remineralizing compound in prevention of microhardness reduction, and showed that the erosive potential of iron drop was much higher than the remineralizing effect of this compound.

The second objective of the present study was to assess the mineral content of enamel of primary teeth after the application of remineralizing agents and exposure to iron drop. The results of EDS analysis showed an increase in calcium content of primary enamel in the final step in MI varnish, CPP-ACP, and FV groups. CPP-ACP and MI varnish remineralizing agents have CPP complexes that increase the mineral content of the teeth. CPP competes with calcium in binding to plaque calcium binding sites, limiting mineral loss in the process of caries development, and creating a super-saturated state of calcium and phosphorous close to the tooth surface, resulting in enhancement of remineralization [33].

Moreover, tooth halves subjected to iron drop and remineralizing agents had higher iron content and lower calcium content than the other halves subjected to re-

mineralizing agents alone. Kharazmi iron with a pH of approximately 1.9 [24] can cause demineralization and enamel erosion. To overcome this acidic pH, the tooth structure releases calcium and phosphate, and becomes porous and Iron ions react with the phosphates [18, 33]. In a study by Salman *et al.* [21] evaluating the effect of remineralizing agents on demineralized lesions used EDS analysis, MI varnish increased the mineral content significantly more than FV.

In the present study, the fluoride element was also analyzed in EDS but no significant difference was noted in this respect among different groups. Similarly, in the study of Vicente *et al.* [35] on prevention of enamel demineralization by fluoride varnishes, no significant difference was found regarding the amount of fluoride ions. They stated that the storage environment affects the amount and speed of release of fluoride. Perhaps the reason for the lack of difference in enamel fluoride levels between the groups is due to the topical application of fluoride, which initially leads to the formation of calcium fluoride on the enamel surface, and later enters the enamel structure. Since EDS analysis detects fluoride within the enamel structure, no difference in the amount of enamel fluoride was observed [25, 34].

Evaluation of the efficacy of commonly used remineralizing agents in pediatric dentistry for prevention of microhardness reduction by Kharazmi iron drop for the first time was the main strength of the present study. Moreover, in addition to measurement of microhardness, EDS analysis was performed, and pH cycling was conducted to simulate the oral environment. Besides, tooth halves were used to compare remineralization plus iron drop and remineralization alone in the same tooth to eliminate the confounding effect of structural differences of the teeth on the results. The *in vitro* design of this study may limit the generalization of results to the oral environment.

Conclusion

Within the limitations of this study, the results showed that application of FV, CPP-ACP, and MI varnish remineralizing agents increased the primary enamel microhardness. Moreover, applying remineralizing agents prior to iron drop exposure prevented microhardness reduction by approximately 10%. MI varnish was significantly more effective than CPP-ACP and FV for this

purpose. Since iron drop exposure significantly decreased the microhardness of primary enamel, CPP-ACP, MI varnish, and fluoride varnish were effective in prevention of reduction in mineral content following exposure to iron drop.

Acknowledgements

Not applicable

Support

None

Funding

No funds, grants, or other support was received.

Conflict of Interests

The authors declare that they have no conflict of interests.

References

- [1] Tabari M, Alaghemand H, Rabiee M, Khefri S, Ahadi MS, Nikpour MR. The effect of silicone oil and nano-hydroxyapatite/chitosan powder on microhardness and surface structure of primary teeth enamel after iron drop consumption. *JDS*. 2013; 31: 138-147.
- [2] Eskandarian T, Motamedifar M, Hekmatfar S, Tamaddon AM. Comparison of the effect of three types of iron drops on surface roughness of deciduous teeth in a simulated cariogenic environment. *JDS*. 2013; 31: 15-22.
- [3] Mehran M, Bassir MM, Jafari S. Effect of two kinds of iron drops on the discoloration, atomic absorption and structural changes of primary teeth enamel. *JDM*. 2009; 21: 1-10.
- [4] Thierens LAM, Moerman S, Elst CV, Vercruyse C, Maes P, Temmerman L, et al. The *in vitro* remineralizing effect of CPP-ACP and CPP-ACPF after 6 and 12 weeks on initial caries lesion. *J Appl Oral Sci*. 2019; 27: e20180589.
- [5] Hekmatfar S, Piraneh H, Jafari K. Evaluation of the relationship between pH and titrable acidity of five different of iron supplements with the absorption of iron ions in the anterior primary teeth (an *in vitro* study). *Dent Res J (Isfahan)*. 2018; 15: 367-371.
- [6] Mozafar S, Ahmadi R, Kameli S, Khodakarami S. *In vitro* efficacy of sodium bicarbonate powder and pumice flour for removal of iron induced pigmentations. *JIDA*. 2019; 31: 154-161.
- [7] Asgari I, Soltani S, Sadeghi SM. Effects of iron products

- on decay, tooth microhardness, and dental discoloration: a systematic review. *Arch Pharm Pract.* 2020; 11: 60-82.
- [8] Karimi M. Does iron drop cause dental caries in children? *J Dent Health Oral Disord Ther.* 2018; 9: 300.
- [9] Valian A, Moezzzadeh M, Moravejsalehi E. Role of Amorphous Calcium Phosphate in Dentistry. *JDS.* 2014; 32: 53-63.
- [10] Ghafournia M, Tehrani MHNA. Casein Phosphopeptides in oral and dental health. *JIDS.* 2009; 4: 211-218.
- [11] Nourolahian H, Parisay I, Mir F. The effect of Remin Pro on the microhardness of initial enamel lesions in primary teeth: An in vitro study. *Dent Res J (Isfahan).* 2021; 18: 16.
- [12] Al-Batayneh OB, Jbarat RA, Al-Khateeb SN. Effect of application sequence of fluoride and CPP-ACP on remineralization of white spot lesions in primary teeth: An in vitro study. *Arch Oral Biol.* 2017; 83: 236-240.
- [13] Duraisamy V, Xavier A, Nayak UA, Reddy V, Rao AP. An in vitro evaluation of the demineralization inhibitory effect of F(-) varnish and casein phosphopeptide-amorphous calcium phosphate on enamel in young permanent teeth. *J Pharm Bioallied Sci.* 2015; 7: S513-S517.
- [14] Thakkar PJ, Badakar CM, Hugar SM, Hallikerimath S, Patel PM, Shah P. An in vitro comparison of casein phosphopeptide-amorphous calcium phosphate paste, casein phosphopeptide-amorphous calcium phosphate paste with fluoride and casein phosphopeptide-amorphous calcium phosphate varnish on the inhibition of demineralization and promotion of remineralization of enamel. *J Indian Soc Pedod Prev Dent.* 2017; 35: 312-318.
- [15] Abufarwa M, Noureldin A, Campbell PM, Buschang PH. The longevity of casein phosphopeptide-amorphous calcium phosphate fluoride varnish's preventative effects: Assessment of white spot lesion formation. *Angle Orthod.* 2019; 89: 10-15.
- [16] Mohammed NI, Mostafa IE, Abdelaziz AA. Evaluation of the effect of different remineralizing agents on stains absorption and surface roughness of freshly bleached teeth (An in vitro study). *AJDSM.* 2018; 21: 307-312.
- [17] Sulieman M. An overview of tooth discoloration: extrinsic, intrinsic and internalized stains. *Dent Update.* 2005; 32: 463-471.
- [18] Pasdar N, Alaghehmand H, Mottaghi F, Tavassoli M. Experimental study of iron and multivitamin drops on enamel microhardness of primary tooth. *J Int Soc Prev Community Dent.* 2015; 5: 518-524.
- [19] Shabzندهdar M, Makarem A, Orafi H, Khashayarmansh Z, Ebrahimzadeh S. Comparison of primary enamel discoloration caused by the use of three different iron drops. *J Dent Mashhad Univ Med Sci.* 2006; 30: 247-254.
- [20] Firouzmandi M, Mohaghegh M, Jafarpisheh M. Effect of silver diamine fluoride on the bond durability of normal and carious dentin. *J Clin Exp Dent.* 2020; 12: e468-e473.
- [21] Salman NR, ElTekeya M, Bakry N, Omar SS, El Tantawi M. Comparison of remineralization by fluoride varnishes with and without casein phosphopeptide amorphous calcium phosphate in primary teeth. *Acta Odontol Scand.* 2019; 77: 9-14.
- [22] Craig RG, Peyton FA. The microhardness of enamel and dentin. *JDR.* 1958; 37: 661-668.
- [23] Salman NR, El-Tekeya MM, Bakry NS, Soliman S. Remineralization effect of fluoride varnish containing casein phosphopeptide amorphous calcium phosphate on caries-like lesions in primary teeth (in vitro study). *ADJALEXU.* 2019; 44: 13-16.
- [24] Sahebazar N, Tavassoli-Hojjati S, Aghaei S. Effect of Sucrosomial(®) Iron and Iron Drop Diluted with Natural Fruit Juice on Microhardness of Primary Enamel. *Front Dent.* 2022; 19: 35.
- [25] Oliveira MRC, Oliveira PHC, Oliveira LHC, Horliana A, César PF, Moura SK, et al. Microhardness of bovine enamel after different fluoride application protocols. *Dent Mater J.* 2019; 38: 61-67.
- [26] Abbasi M, Mazhari F, Jaafari MR, Afshari E, Bagheri H, Parisay I. Color change of primary teeth following exposure to an experimentally synthesized liposomal nano-encapsulated ferrous sulfate drop versus the commercially available iron drops. *PDJ.* 2021; 31: 256-267.
- [27] Maguire A, Baqir W, Nunn JH. Are sugars-free medicines more erosive than sugars-containing medicines? An in vitro study of paediatric medicines with prolonged oral clearance used regularly and long-term by children. *Int J Paediatr Dent.* 2007; 17: 231-238.
- [28] Nanci A. *Ten Cate's Oral Histology.* 9th ed. St Louis, Missouri: Elsevier; 2017. p. 523-525.
- [29] Martinhon CC, Italiani Fde M, Padilha Pde M, Bijella MF, Delbem AC, Buzalaf MA. Effect of iron on bovine enamel and on the composition of the dental biofilm formed "in situ". *Arch Oral Biol.* 2006; 51: 471-475.
- [30] Magalhães AC, Moraes SM, Rios D, Buzalaf MA. Effect of iron supplementation of a commercial soft drink on too-

- th enamel erosion. Food Addit Contam Part A Chem Anal Control Expo Risk Assess. 2009; 26: 152-156.
- [31] Sales-Peres SH, Pessan JP, Buzalaf MA. Effect of an iron mouthrinse on enamel and dentine erosion subjected or not to abrasion: an in situ/ex vivo study. Arch Oral Biol. 2007; 52: 128-132.
- [32] Mittal S, Singh B, Sharma A, Mittal K, Justa A, Vaid P. Surface changes of primary tooth enamel by commonly used pediatric liquid medicaments: A scanning electron microscope study. JP Dent. 2017; 5: 14-20.
- [33] Fernando JR, Shen P, Sim CPC, Chen YY, Walker GD, Yuan Y, et al. Self-assembly of dental surface nanofilaments and remineralisation by SnF₂ and CPP-ACP nanocomplexes. Sci Rep. 2019; 9: 1285.
- [34] Ebrahimi M, Mehrabkhani M, Ahrari F, Parisay I, Jahantigh M. The effects of three remineralizing agents on regression of white spot lesions in children: A two-week, single-blind, randomized clinical trial. J Clin Exp Dent. 2017; 9: e641-e648.
- [35] Vicente A, Ortiz Ruiz AJ, González Paz BM, García López J, Bravo-González LA. Efficacy of fluoride varnishes for preventing enamel demineralization after interproximal enamel reduction. Qualitative and quantitative evaluation. PLoS One. 2017; 12: e0176389.