

Systematic Review

Bond Strength Evaluation of Ceramic Restorations with Immediate Dentin Sealing: A Systematic Review and Meta-Analysis

Pooran Samimi¹, MSc; Pedram Iranmanesh², MSc; Maryam Khoroushi¹, MSc; Mohammad Hossein Kafi³, MSc; Niloufar Jafari⁴, MSc;

¹ Dept. of Operative Dentistry, Dental Materials Research Center, Dental Research Institute, School of Dentistry, Isfahan University of Medical Sciences, Isfahan, Iran.

² Dept. of Endodontics, Dental Research Center, Dental Research Institute, School of Dentistry, Isfahan University of Medical Sciences, Isfahan, Iran.

³ Dept. of Endodontics, School of Dentistry, Rafsanjan University of Medical Sciences, Rafsanjan, Iran.

⁴ Dept. of Operative Dentistry, School of Dentistry, Rafsanjan University of Medical Sciences, Rafsanjan, Iran.

KEY WORDS

Dentin;
Bonding Agents;
Resin cement;
Shear Strength;
Tensile Strength;

Received: 14 December 2022;

Revised: 12 March 2023;

Accepted: 27 May 2023;

Copyright

© Journal of Dentistry, this is an open access article distributed under the terms of the Creative Commons Attribution 4.0 International License, (<http://creativecommons.org/licenses/by/4.0/>) which permits reusers to copy and redistribute the material in any medium or format if the original work is properly cited, and attribution is given to the creator. The license also permits for commercial use.

ABSTRACT

Statement of the Problem: Immediate dentin sealing (IDS) was introduced to overcome the disadvantages of delayed dentin sealing like pollution of dentin tubules, microleakage, and bond strength destruction over time. The effect of IDS on the bond strength of indirect restorations is still debatable.

Purpose: This study was conducted to determine the effect of IDS on the bond strength of ceramic restorations to dentin.

Materials and Method: In this systematic review and meta-analysis, the study protocol was registered on the PROSPERO database under the registration number CRD420202014 27. MEDLINE (PubMed), Web of Science, Scopus, and ProQuest databases were searched until January 2021 and updated in January 2022. Worldcat.org and Opengrey.eu, ProQuest dissertation and thesis, and Google Scholar were searched to explore the grey literature. The *in vitro* studies evaluating the bond strength of ceramic restoration to dentin with and without IDS were included. Seven criteria were assessed to evaluate the risk of bias in the study. Statistical analyses were conducted using RevMan 5.3. The inverse variance method was used to determine the mean difference of micro-tensile bond strength (μ TBS) and shear bond strength (SBS).

Results: A total of 10 studies (20 datasets) were included in the meta-analysis. Regarding the μ TBS analysis, IDS had a significantly higher bond strength than Delayed Dentin Sealing (DDS) (MD:1.16, 95%CI:0.28_2.03, $I^2=0\%$). However, no significant difference was found between them in the SBS analysis (MD:0.25, 95%CI: -0.56-1.06, $I^2=96\%$). All studies were categorized to have a moderate or high risk of bias.

Conclusion: Most *in vitro* evidence showed favorable results for the effect of IDS on the bond strength and durability of indirect restorations. The adhesive system and the type of ceramic and its treatment before cementation are determining factors. Due to the heterogeneity of the outcomes and studies with a moderate/high risk of bias, the quality of the evidence was low.

Corresponding author: Jafari N, Dept. of Operative Dentistry, School of Dentistry, Rafsanjan University of Medical Sciences, Rafsanjan, Iran. Tel: +98-9103737322 Fax: +98-3434280028
Email: Niloufarjafari94@gmail.com

Cite this article as: Samimi P, Iranmanesh P, Khoroushi M, Kafi MH, Jafari N. Bond Strength Evaluation of Ceramic Restorations with Immediate Dentin Sealing: A Systematic Review and Meta-Analysis. *J Dent Shiraz Univ Med Sci.* September 2024; 25(3): 192-202.

Introduction

The use of tooth-colored materials to restore decayed

teeth, particularly in the posterior areas of the mouth, is important for many patients [1]. The direct use of com-

posite resins for the reconstruction of teeth where gross tooth destruction has occurred and requires a vast reconstruction, especially the proximal contours, is too challenging and sometimes even impossible [2]. In these situations, the use of indirect restorations allows accurate reconstruction of the tooth crown and has better contours, wear resistance, and mechanical strength than the direct ones [2-3].

However, the disadvantages of indirect restorations such as tooth sensitivity that occasionally occurs in vital teeth, bond strength reduction over time, debonding, secondary caries, and fractures should be noted since they compromise the survival rate [4-5]. Hence, the improvement of bond strength is an important factor to enhance the success rate and fracture resistance, decrease micro-leakage, and increase the overall survival rate [6].

The conventional method used for the cementation of indirect restoration is delayed dentin sealing (DDS), which briefly includes the application of adhesive resins just before cementation [7-10]. Resin coating technique was introduced by Pashley *et al.* [11] in the 1990s to improve the properties of indirect restorations and to reduce tooth sensitivity. Later in 2005, Magne *et al.* [12] introduced immediate dentin sealing (IDS) based on the resin coating technique. This procedure involves the sealing of freshly cut dentin tubules filled with an adhesive resin alone or in combination with a low-viscosity resin prior to (digital or analog) impression-taking [12]. The use of IDS has been effective in improving the bond strength of indirect restorations [13-16]; however, some studies have indicated no priority for DDS regarding the long-term bond strength [17].

Considering the lack of consistency among the results of studies on the effect of IDS on the bond strength of indirect restorations and the lack of a comprehensive review in this field, this systematic review and meta-analysis aimed to evaluate the effect of IDS on the bond strength of ceramic restorations.

Materials and Method

Protocol and registration

The study protocol was registered on the PROSPERO database under the registration number CRD4202020-14 27. The Preferred Reporting Items for Systematic Reviews and Meta-Analyses (PRISMA) checklist was used to report this systematic review [18].

Forming the question

The research question, based on the patient, intervention comparison, outcome, study (PICOS) framework, was “Does IDS improve the bond strength of ceramic restorations to dentin in comparison with IDS in experimental studies?”

The PICOS framework was set as P: human teeth with ceramic restoration, I: IDS, C: DDS, O: effect on micro-tensile bond strength (μ TBS) or shear bond strength (SBS), and S: experimental studies.

Study eligibility criteria

The inclusion criteria were all experimental studies that evaluated the SBS or μ TBS of ceramic restorations to dentin using IDS. The exclusion criteria were studies that evaluated properties other than the bond strength of ceramic restorations to dentin, studies that evaluated the bond strength of other types of restorative materials, clinical trials, all types of reviews, case reports, or case series.

Information sources and search strategy

The keywords in the search strategy were defined based on the PICOS framework. An unlimited literature search was undertaken on the MEDLINE (PubMed), Web of Science, Scopus, and ProQuest databases. Worldcat.org and Opengrey.eu, ProQuest dissertation and thesis, and the first 100 results in Google Scholar were searched to explore the grey literature until January 2021 and updated in January 2022. A manual search was performed to explore the reference lists of all primary studies for the additional relevant publications linked to each primary study on the PubMed database. The search strategies in the four main databases are listed in Table 1. The search was restricted to English language.

Study selection and data collection

After the removal of the duplicate studies, the records were selected by titles and abstracts. In the next stage, full-text articles were screened for including records meeting the inclusion criteria. The study selection was done by two researchers independently, and any disagreement was resolved through discussion with other reviewers. Google sheets software was used as a customized extraction form to extract relevant data. The extraction form consisted of the first author's name, year of publication, number of samples, adhesive system for IDS, type of aging protocol (mechanical or thermal or

Table 1: Search strategy of the databases from their foundation until January 2021 and updated January 2022

Database	Search line	Number of retrieved records
MEDLINE (PubMed)	("immediate dentin sealing" OR "dentin sealing" OR "resin coating") AND ("bond strength" OR "Shear bond" OR "tensile bond")	78
Scopus	TITLE-ABS-KEY (("bond strength" OR "Shear bond" OR "tensile bond") AND ("immediate dentin sealing" OR "dentin sealing" OR "resin coating"))	94
Web of Science	TS= (((("immediate dentin sealing" OR "dentin sealing" OR "resin coating") AND ("bond strength" OR "Shear bond" OR "tensile bond"))	90
ProQuest	("immediate dentin sealing" OR "dentin sealing" OR "resin coating") AND ("bond strength" OR "Shear bond" OR "tensile bond")	309

none), type of luting agent, type of ceramic, porcelain treatment before cementation, and main outcome. Data were extracted by two reviewers independently, and any disagreement was resolved via discussion with other reviewers. In case of missing data, an email was sent to the corresponding author. If the authors did not answer up to one month twice, the record was excluded.

Quality assessment

The quality assessment of each included study was independently assessed by two reviewers using the checklist of other systematic reviews [19]. The parameters consisted of (1) randomization of teeth, (2) use of teeth free of caries or restoration, (3) use of materials according to the manufacturer's instructions, (4) use of teeth with similar dimensions, (5) description of sample size calculation, (6) treatment performed by the same operator, and (7) blinding of the operator of the testing machine. If it was possible to find the information in the article, it received an "Y" (yes) answer and vice versa. Studies that reported one to three items were classified as high risk of bias, four or five items as a medium risk of bias, and six or seven items as a low risk of bias. Any disagreements were resolved through discussion with a third reviewer.

Synthesis of results

The data of each study were fed into RevMan 5.3 (The Cochrane Collaboration, Copenhagen, Denmark). Mean difference (MD) was determined for μ TBS and SBS by inverse variance method. For subgroup analysis, studies were divided based on the bonding system used for the IDS, cement type, and ceramic restoration type and ceramic treatment before cementation. Statistical heterogeneity of the treatment effect was assessed using the inconsistency I^2 test in which values greater than 75% were considered highly heterogeneous [20]. The sensitivity analysis was conducted by removing the studies with a high risk of bias.

Results

Study selection

A total of 892 relevant records were extracted from the databases. Figure 1 is a PRISMA flowchart that summarizes the article selection process. After the removal of duplicates, 321 records were evaluated for the titles and abstracts, from which 291 records were excluded. Therefore, 30 records were subjected to full-text evaluation. Of them, 20 studies were excluded. Table 2 shows the records excluded with reasons in the full-text assessment phase. Finally, 10 records [4, 7-8, 13, 15-17, 21-23] were used for qualitative and quantitative synthesis. Ten studies were included, of which 4 studies used μ TBS test and 6 used SBS test.

Characteristics of the included datasets

As for μ TBS test, all datasets used a non-self-adhesive luting system for the ceramic cementation and evaluated the bond strength of silica-based ceramics. Except one dataset, self-etch adhesive systems were used for IDS in other datasets [23] (Table 3). Regarding SBS test, all studies except one [17] used non-self-adhesive resin cement and all of the studies evaluated the bond strength of silica-based ceramics to teeth except one [13] which evaluated the bond strength of non-silica-based ceramics (monolithic zirconia). This study used two different materials for cementation (with Panavia F2 or PermaCem). It is noteworthy that only Panavia results were included for better comparison, the same as

Table 2: Studies excluded with reasons in the full-text assessment phase; IDS: immediate dentin sealing, DDS: delayed dentin sealing

Reasons for exclusion	References
Evaluation of the effects of IDS on the bond strength of cement to ceramic	n=1
Evaluation of the effect of IDS on the bond strength of metal restorations to teeth	n=1
Evaluation of the effect of IDS on the bond strength of laboratory or chair side or CAD CAM resin composite to teeth	n=17
Not having DDS as a control group	n=1

Table 3: Studies that used μ TBS

Study	Adhesive system	Sample size per group (N)	Type of aging	Type of luting agent	Type of ceramic	Porcelain treatment before cementation	IDS/ mean (Mpa) (SD)	DDS/ mean (Mpa) (SD)
Ishi <i>et al.</i> [21]	Etch-and-rinse	4	Artificial mechanical	Non-self-adhesive	Silica-based	Airborne Particle Abrasion (APA)	5.1(1.2)	3.5(1.6)
Hayashi <i>et al.</i> [16]	Self-etch	30	Artificial mechanical	Non-self-adhesive	Silica-based	Hydrofluoric acid (HF)	4.9(2.0)	3.8(1.7)
Kitayama* <i>et al.</i> [22]	Self-etch	14	Artificial mechanical	Non-self-adhesive	Silica-based	Airborne Particle Abrasion (APA)	12.97(5.82): N (60/98) (Number of beams, tested/total)	– (0/89)
Kitayama. <i>et al.</i> [22]	Self-etch	14	No	Non-self-adhesive	Silica-based	Airborne Particle Abrasion (APA)	15.17 (5.24): N (49/81)	15.82 (4.22): N (45/78)
Murata** <i>et al.</i> [4]	Self-etch	8	Artificial mechanical	Non-self-adhesive	Silica-based	n/a	5.8(2.3)	4.4(1.5)

IDS: immediate dentin sealing, DDS: delayed dentin sealing, n/a: Not applicable, HF: Hydrofluoric acid, APA: Airborne particle abrasion, CJ: CoJet
Superscript letters show different datasets from one study.

* Samples with artificial aging were not included because all samples in the DDS group failed in the pretest.

** Three different IDS applications were used, but just one of them was included in the analysis because this method was more similar to other included studies.

other included studies (Table 4). Each study in both categories used a different protocol for porcelain treatment before cementation, e.g. etching by Hydrofluoric acid (HF), Airborne-Particle Abrasion (APA), CoJet (CJ) abrasion, or none. There was a huge variation in the aging protocols in both categories.

Risk of bias in individual studies

Overall, in the μ TBS group, all studies were categorized

as moderate (1 study; 25%) or high risk of bias (3 studies; 75%). In the SBS group, four (66.6%) and two (33.3%) studies showed a moderate and high risk of bias, respectively. No studies (100%) in each group mentioned sample size calculation and blinding of the operator of the testing machine. Moreover, 100% and 66.6% of studies in the μ TBS and SBS groups did not mention the treatment was performed by a single oper-



2009 Flow Diagram
PRISMA

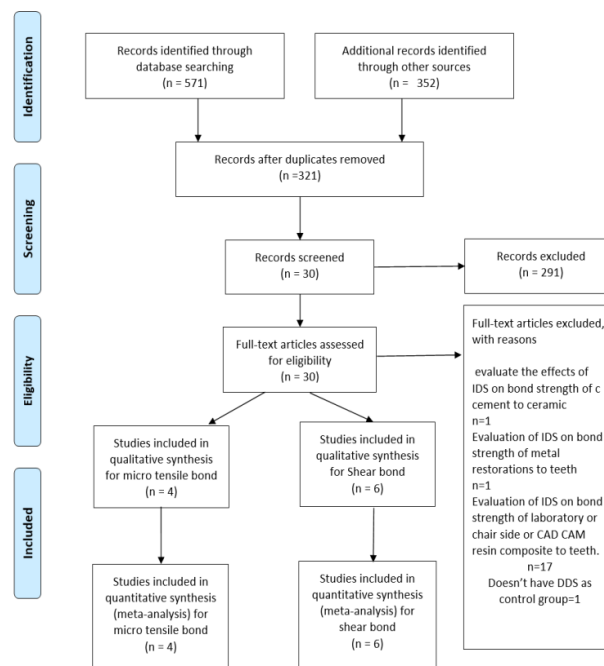


Figure 1: Preferred reporting items for systematic reviews and meta-analyses flow diagram of the search processes

Table 4: Studies that used SBS test

Study	Adhesive System	Sample size pre group (n)	Type of aging	Type of luting agent	Type of ceramic	Porcelain treatment before cementation	IDS/ mean (Mpa) (SD)	DDS/ mean (Mpa) (SD)
Falkensammer <i>et al.</i> [7]	Self-etch	48	No	Non-self-adhesive	Silica-based	Hydrofluoric acid (HF)	13.7(4.7)	19.5(4.0)
Shakal* <i>et al.</i> [8]	Etch-and-rinse	10	Artificial thermal	Non-self-adhesive	Silica-based	Airborne Particle Abrasion (APA)	7.50(0.78)	8.00(0.31)
Shakal <i>et al.</i> [8]	Etch-and-rinse	10	No	Non-self-adhesive	Silica-based	Airborne Particle Abrasion (APA)	9.42(0.56)	10.06(0.44)
Shakal <i>et al.</i> [8]	Etch-and-rinse	10	Artificial thermal aging	Non-self-adhesive	Silica-based	Hydrofluoric acid (HF)	8.00(0.79)	8.82(0.389)
Shakal <i>et al.</i> [8]	Etch-and-rinse	10	No	Non-self-adhesive	Silica-based	Hydrofluoric acid (HF)	8.14(0.44)	8.86(0.384)
Shakal <i>et al.</i> [8]	Etch-and-rinse	10	Artificial thermal aging	Non-self-adhesive	Silica-based	CoJet (CJ)	7.62(0.49)	8.10(0.22)
Shakal <i>et al.</i> [8]	Etch-and-rinse	10	No	Non-self-adhesive	Silica-based	CoJet (CJ)	8.14(0.44)	10.50(0.41)
Shakal <i>et al.</i> [8]	Etch-and-rinse	10	Artificial thermal aging	Non-self-adhesive	Silica-based	N	4.44(0.52)	4.88(0.544)
Shakal <i>et al.</i> [8]	Etch-and-rinse	10	No	Non-self-adhesive	Silica-based	N	6.00(0.79)	7.52(0.37)
Reboul <i>et al.</i> [23]	Etch-and-rinse	10	No	Non-self-adhesive	Silica-based	Hydrofluoric acid (HF)	15.74 (2.12)	12.07(1.41)
Choi** <i>et al.</i> [15]	Etch-and-rinse	10	Artificial thermal aging	Non-self-adhesive	Silica base	Hydrofluoric acid (HF)	4.11(2.82)	3.14(1.47)
Choi <i>et al.</i> [15]	Self-etch	10	Artificial thermal aging	Non-self-adhesive	Silica-bases	Hydrofluoric acid (HF)	11.18 (4.75)	3.14 (1.47)
Dalby*** <i>et al.</i> [17]	Etch-and-rinse	13=Opti bond FL 11=single bond 11=DDS	No	Self-adhesive	Silica-based	Hydrofluoric acid (HF)	10.03(3.50) 8.24(3.35)	7.17(2.09)
Dalby <i>et al.</i> [17]	Self-etch	8 samples=Go! 11 samples= one coat bond 11 samples in DDS group	No	Self-adhesive	Silica-based	Hydrofluoric acid (HF)	6.94 (1.53) 7.21(2.83)	7.17(2.09)
Rigos**** <i>et al.</i> [13]	Etch-and-rinse	15	No	Non-self-adhesive	Non-silica-based	Airborne Particle Abrasion (APA)	39.94 (1.34)	33.40 (1.76)
Rigos <i>et al.</i> [13]	Etch-and-rinse	15	No	Non-self-adhesive	Non-silica-based	CoJet (CJ)	38.68 (1.16)	29.37(2.16)

* According to different porcelain treatment before cementation and aging or non-aging variables included in eight datasets
 ** Each included two datasets according to different adhesive systems.
 *** Assessed in two data sets according to different porcelain treatment before cementation

ator. Hence, at least three out of seven items received NO answers for included studies, and none of them was categorized as a low risk of bias (Tables 5 and 6).

Meta-analysis

The meta-analysis indicated that IDS had no positive effect on the SBS (MD:0.25, 95%CI: -0.56-1.06, I²=

Table 5: Assessment of the risk of bias of μTSB (n = 4)

Study	Tooth randomization	Teeth free of caries or restoration	Materials used according to the manufacturer's instructions	Teeth with similar dimensions	Sample size calculation	Treatment performed by a single operator	Blinding of the operator of the testing machine	Risk of bias
Maeno <i>et al.</i> [16]	N	Y	Y	Y	N	N	N	High risk
Kitayama <i>et al.</i> [22]	Y	Y	Y	Y	N	N	N	Moderate risk
Maeski <i>et al.</i> [4]	N	Y	Y	Y	N	N	N	High risk
Ishi <i>et al.</i> [21]	N	Y	Y	Y	N	N	N	High risk

Table 6: Assessment of the risk of bias of shear bond strength (SBS) (n = 6)

Study	Tooth randomization	Teeth free of caries or restoration	Materials used According to the manufacturer's instructions	Teeth with similar dimensions	Sample size calculation	Treatment performed by a single operator	Blinding of the operator of the testing machine	Risk of bias
Falkensammer <i>et al.</i> [7]	No	Yes	Yes	Yes	No	No	No	High risk
Choi <i>et al.</i> [15]	Yes	Yes	Yes	Yes	No	No	No	Moderate risk
Dalby <i>et al.</i> [17]	Yes	Yes	Yes	Yes	No	Yes	No	Moderate risk
Shakal <i>et al.</i> [8]	Yes	Yes	Yes	N	No	No	No	High risk
Reboul <i>et al.</i> [23]	Yes	Yes	Yes	Yes	No	Yes	No	Moderate risk
Rigos <i>et al.</i> [13]	Yes	Yes	Yes	Yes	No	No	No	Moderate risk

“Y” = “Yes” and shows reported item “N” = “No” and shows not reported item

96%) (Figure 2). In subgroup analysis, IDS demonstrated no positive effect on the SBS when silica-based ceramics were used (MD: -0.36, 95%CI: -1.00-0.27, $I^2=93%$). Likewise, in subgroup analysis, IDS demonstrated no positive effect on the SBS when non-self-adhesive cements were used as a luting agent (MD: 0.12, 95%CI: -0.73-0.96, $I^2=97%$). The results of the analysis of non-artificial and artificial aging datasets showed no statistically significant difference (MD: -0.12, 95%CI: -1.64-1.40, $I^2=98%$ and MD: -0.10, 95%CI: -0.77-0.57, $I^2=85%$), respectively). Although applying etch-and-rinse systems for IDS did not improve the SBS (MD:1.06, 95%CI: 0.36-2.09, $I^2=98%$), the self-etch systems enhanced the SBS (MD:0.66, 95%CI:-6.38-7.69), $I^2=97%$).

The meta-analysis indicated that IDS had a positive effect on the μ TBS (MD:1.16, 95%CI:0.28_2.03, $I^2=0%$) (Figure 3). In subgroup analysis, IDS improved

the μ TBS after aging or applying self-etch adhesive systems (MD:1.27, 95%CI:0.37-2.18, $I^2=0%$ and MD: 1.04, 95%CI: 0.07-2.05, $I^2=0%$, respectively).

The results of sensitivity analysis (after eliminating the high-risk studies) in both SBS and μ TBS categories showed that MD was significantly higher in DDS than in IDS (MD:4.13 95%CI:078-7.48, $I^2=96.5%$ and MD:-0.65 95%CI:-4.17-2.78, $I^2=NA$, respectively), which was different from the main analysis. Hence, the robustness of the analysis was low.

Discussion

IDS was first introduced in 2005 to improve adhesion and restorative adaptation and to protect the pulp vitality [24]. The primary technique involves the application of an etch-and-rinse adhesive to the dentin surface. After taking the impression in the delivery session, an indirect restoration was applied after sandblasting with

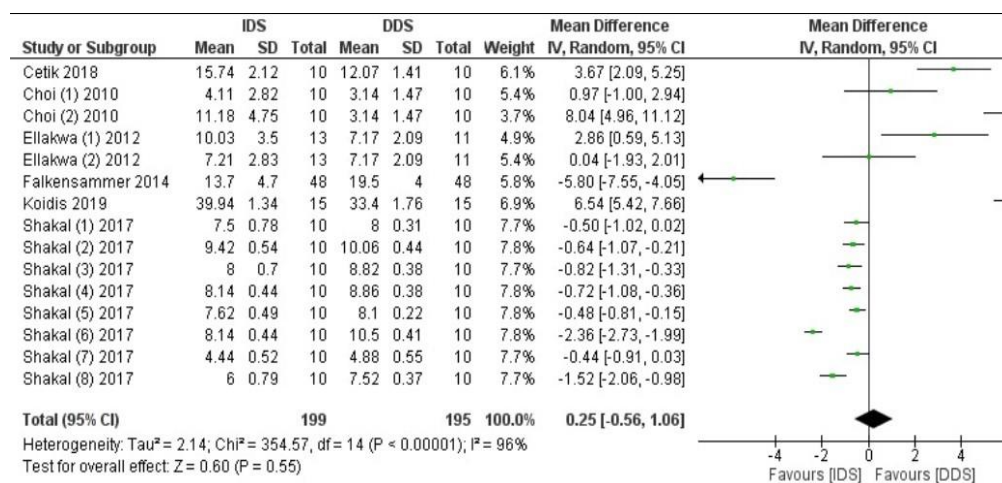


Figure 2: Forest plot of the analysis of immediate dentin sealing (IDS) on shear bond strength (SBS) compared to Delayed Dentin Sealing (DDS). Event: shear bond strength (SBS) in Mpa

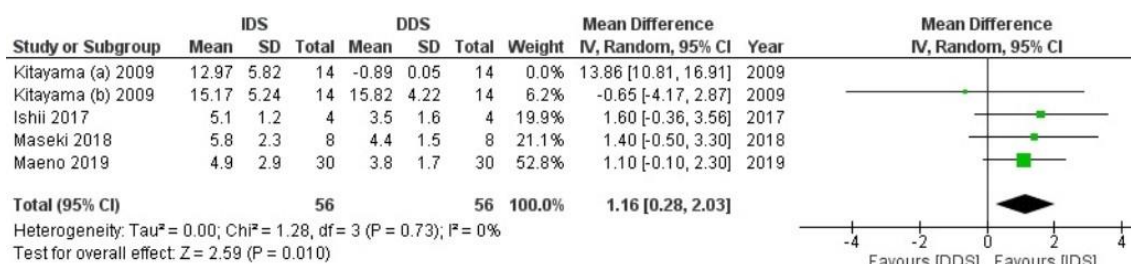


Figure 3: Forest plot of the analysis of immediate dentin sealing (IDS) on μ TBS compared to delayed dentin sealing (DDS). Event: μ TBS in Mpa

a non-self-adhesive cement on the IDS surface, which was conditioned by a brush and pumice [12]. Since then, different IDS methods with different types of bonding, intaglio surface preparation methods, IDS surface conditioning, and direct and indirect restorations with different materials have been studied, which have shown different results [25-28]. Therefore, the outcome of the present study may help practitioners make better clinical decisions.

The results of the included studies according to the test used for measuring bond strength were assessed in two categories: SBS and μ TBS. The present meta-analysis showed that μ TBS was higher with IDS than with DDS, and there was no significant difference between the two groups in SBS. The SBS has easy sample preparation and less technical sensitivity, but the samples in μ TBS can be highly affected by adverse events such as premature failures and need a larger number of samples [25-28]. Yet, the more uniform stress distribution achieved by the μ TBS test than the SBS [29] is a considerable factor, so the simplicity of the SBS test seems not to be a good reason for choosing this test to evaluate the bond strength [30].

In case of mechanical or thermal aging of the samples, the μ TBS of IDS was higher than that of DDS, but the difference was not significant in the SBS analysis. Thus, the use of IDS may increase the bonding durability. The positive effect of IDS on durability is probably due to the sufficient and effective penetration of the resin into the newly cut dentin collagen fibers of the tooth and the formation of a sufficiently thick hybrid layer compared to DDS. In the absence of dentin sealing, the collagen fibers collapse during impression-taking, and their interfibrillar spaces are reduced for the resin to penetrate [31-32]. On the other hand, in the case of temporary restoration, even despite the use of various surface cleaning methods to remove cement residues (such as air-abrasion), dentin is contaminated

with temporary cement and prevents adequate interaction between the adhesive and collagen [33]. If temporary restoration is not used, or restoration does not have enough sealing, the dentin becomes contaminated, and all these factors interfere with the penetration of the resin and the formation of an effective hybrid layer, which endangers the immediate bond strength of the dentin [34].

IDS also prevents the denaturation of collagen structure over time by sealing tubules and preserving exposed collagen in the freshly cut dentin and preventing the contamination and activation of proteolytic enzymes [35, 36]. Furthermore, this layer acts as a stress reliever and protects the bonding layer against mechanical forces [4]. Another positive effect is due to the maturation of the adhesive layer (IDS) by the dark curing mechanism and the continuation of polymerization until the cementation is performed. This process reduces the stresses due to the polymerization of the cement and the occlusal forces on the newly created hybrid layer with low strength compared to DDS [37-38]. Since the bond strength decreases over time, according to the results, it may be possible to confirm the results of previous studies about the effect of IDS on increasing the bond durability [12, 16].

The bond strength, in terms of the type of adhesive system, indicated that although the SBS of IDS was not higher in the etch-and-rinse system, the μ TBS of IDS was higher in the self-etch subgroup. The bonding systems with fillers or functional monomers (creating a chemical bond) in the etch-and-rinse subgroup of the SBS group were used in most studies [39-41], which, if used correctly, create high strength. Thus, IDS can be used with all types of bonding systems to create sufficient film thickness as recommended by Magne *et al.* [42]. It can also be as effective as OptiBond FL, which is the gold standard of adhesive materials.

The μ TBS and SBS of IDS and DDS groups were

the same when different ceramic surface preparation methods were applied before cementing the restoration. However, the bond strength decreased in preparation with silicate, air-abrasion, and hydrofluoric acid, respectively. This result can be due to the dual chemical and mechanical bonding properties of air-abrasion systems with silicate particles and increased surface roughness in air-abrasion compared to hydrofluoric acid [8, 43-44]. Therefore, surface preparation methods are highly effective in improving the bond strength, and the main purpose of using IDS is not to increase the bond strength.

Despite the numerous advantages mentioned for IDS in studies, this technique is time-consuming and requires more materials and steps. This method has a high technical sensitivity. If the adhesive layer is too thick, the strength of ceramic restorations will decrease due to less space and a large difference in the elastic coefficient of the adhesive layer and restorations, especially ceramic restorations [45-46]. On the other hand, if a very thin adhesive layer (less than 40 microns) is formed, all the thickness of the adhesive turns into an air-inhibited layer and the adhesive does not polymerize, and this method practically loses its clinical effectiveness [47]. To reduce the interference of temporary restorations and common impression materials, the tooth should be covered with Vaseline after IDS so that the monomers in the temporary restorative resin are not bonded to the adhesive layer [24, 48]. Moreover, instead of using temporary cement, mechanical gear should be created with the help of undercuts, embracers, and temporary splints, and the final restoration should be delivered and cemented in the shortest possible time (up to 1 week) [49]. To eliminate the interference with the impression materials, it is recommended to use digital impression-taking methods, and if impression materials are used, the oxygen-inhibiting layer of the IDS surface should be thoroughly cleaned and removed to prevent complete polymerization of the impression materials [50-51].

Few clinical studies have investigated the effectiveness of this technique. Gresnigt *et al.* [52] reported that IDS increased the survival rate of restorations if more than 50% of dentin was exposed. However, Van den Breemer *et al.* [53] showed IDS was not superior in the survival rate and success of restorations. The

heterogeneity of the population in terms of oral health and different experiences of clinicians may be the reasons for these contradictions [53].

Due to the lack of clinical trials, the present study was performed on *in vitro* studies. The high heterogeneity of the SBS studies indicates the diversity of the materials and methods used. The quality of most studies in both groups was categorized as moderate to high risk of bias. It should be noted among a seven-item criterion proposed, three criteria of sample size calculation, the blinding of the operator of the testing machine, and performing the treatment by one operator were not mentioned in most studies. Thus, several variables in the design of laboratory studies were not controlled or reported, which might be due to the lack of an accepted guideline. By excluding the high risk of bias studies, the outcome was different from the main outcome for each group, indicating low consistency. Most of the included studies evaluated the SBS. However, owing to the advantages of μ TBS, it is suggested for the bond strength evaluation in this area. More studies with a better design are needed to achieve a definitive result.

Conclusion

Most *in vitro* evidence showed the favorable impact of IDS on the bond strength and durability of indirect restorations. The use of any standard etch-and-rinse adhesive system or self-etching system is effective to obtain the desired results with IDS. The use of pre-treatment ceramic surface preparation methods reduces the difference in the IDS impact. However, the results of the *in vitro* studies should be used in clinical settings with caution. In addition, the included studies have low-quality evidence, so more high-quality research is needed.

Acknowledgement

This study was approved by the Ethics Committee of Isfahan University of Medical Sciences, Isfahan (approval number: IR.MUI.RESEARCH.REC.1399. 603).

Conflict of Interest

The authors declare that they have no conflict of interest.

References

- [1] Lutz F, Krejci I. Resin composites in the post-amalgam age. Compendium of continuing education in dentistry Jamesburg, NJ 1995. 1999; 20: 1138-1148.
- [2] Ritter AV, Walter R, Lee W, Boushell. Sturdevant's art and science of operative dentistry. 7th ed. Elsevier Health Sciences: North Carolina; 2019. p. 220-221.
- [3] Breschi L. Fundamentals of Operative Dentistry: A contemporary approach. 4th ed. Quintessence Publishing: Chicago; 2013. p. 293.
- [4] Murata T, Maseki T, Nara Y. Effect of immediate dentin sealing applications on bonding of CAD/CAM ceramic onlay restoration. Dent Mater J. 2018; 76: 928-939.
- [5] Qanungo A, Aras MA, Chitre V, Mysore A, Amin B, Daswani SR. Immediate dentin sealing for indirect bonded restorations. J Prosthodont Res. 2016; 60: 240-249.
- [6] Krämer N, Lohbauer U, Frankenberger R. Adhesive luting of indirect restorations. Am J Dent. 2000; 13: 60D-76D.
- [7] Falkensammer F, Arnetzl GV, Wildburger A, Krall C, Freudenthaler J. Influence of different conditioning methods on immediate and delayed dentin sealing. J Prosthet Dent. 2014; 112: 204-210.
- [8] Shakal MAS. Evaluation of zirconia-reinforced lithium silicate ceramic surface treatment on their shear bond strength to dentine following immediate dentin sealing. Egypt Dent J. 2017; 63: 3907-3913.
- [9] Vinagre A, Ralho A, Ramos N, Messias A, Ramos J. Bonding performance of a universal adhesive: Effect of hydrophobic resin coating and long-term water storage. Rev Port Estomatol Med Dentária Cir Maxilofac. 2019; 60: 96-103.
- [10] Rozan S, Takahashi R, Nikaido T, Tichy A, Tagami J. CAD/CAM-fabricated inlay restorations: Can the resin-coating technique improve bond strength and internal adaptation? Dent Mater J. 2020; 39: 941-949.
- [11] Pashley DH, Ciucchi B, Sano H, Horner JA. Permeability of dentin to adhesive agents. Quintessence Int. 1993; 24: 618-631.
- [12] Magne P, Kim TH, Cascione D, Donovan TE. Immediate dentin sealing improves bond strength of indirect restorations. J Prosthet Dent. 2005; 94: 511-519.
- [13] Rigos A, Dandoulaki C, Kontonasaki E, Kokoti M, Papadopoulou L, Koidis P. Effect of immediate dentin sealing on the bond strength of monolithic zirconia to human dentin. Oper Dent. 2019; 44: E167-E179.
- [14] Hironaka NG, Ubaldini AL, Sato F, Giannini M, Terada RS, Pascotto RC. Influence of immediate dentin sealing and interim cementation on the adhesion of indirect restorations with dual-polymerizing resin cement. J Prosthet Dent. 2018; 119: 678.
- [15] Choi YS, Cho IH. An effect of immediate dentin sealing on the shear bond strength of resin cement to porcelain restoration. J Adv Prosthodont. 2010; 2: 39.
- [16] Hayashi K, Maeno M, Nara Y. Influence of immediate dentin sealing and temporary restoration on the bonding of CAD/CAM ceramic crown restoration. Dent Mater J. 2019; 38: 970-980.
- [17] Dalby R, Ellakwa A, Millar B, Martin FE. Influence of immediate dentin sealing on the shear bond strength of pressed ceramic luted to dentin with self-etch resin cement. Int J Dent. 2012; 2012: 310702.
- [18] Moher D, Liberati A, Tetzlaff J, Altman DG, PRISMA Group. Preferred reporting items for systematic reviews and meta-analyses: the PRISMA statement. Int J Surg. 2010; 8: 336-341.
- [19] Sarkis-Onofre R, Skupien J, Cenci M, Moraes R, Pereira-Cenci T. The role of resin cement on bond strength of glass-fiber posts luted into root canals: a systematic review and meta-analysis of *in vitro* studies. Oper Dent. 2014; 39: E31-E44.
- [20] Higgins JP, Thompson SG. Quantifying heterogeneity in a meta-analysis. Stat Med. 2002; 21: 1539-1558.
- [21] Ishii N, Maseki T, Nara Y. Bonding state of metal-free CAD/CAM onlay restoration after cyclic loading with and without immediate dentin sealing. Dent Mater J. 2017; 36: 357-367.
- [22] Kitayama S, Pilecki P, Nasser NA, Bravis T, Wilson RF, Nikaido T, et al. Effect of resin coating on adhesion and microleakage of computer-aided design/computer-aided manufacturing fabricated all-ceramic crowns after occlusal loading: a laboratory study. Eur J Oral Sci. 2009; 117: 454-462.
- [23] Reboul T, Thaï HH, Cetik S, Atash R. Comparison between shear forces applied on the overlay-dental tissue interface using different bonding techniques: An *in vitro* study. J Indian Prosthodont Soc. 2018; 18: 212.
- [24] Magne P. Immediate dentin sealing: a fundamental procedure for indirect bonded restorations. J Esthet Restor Dent. 2005; 17: 144-154.
- [25] De Munck J, Vargas M, Iracki J, Van Landuyt K, Poitevin A, Lambrechts P, et al. One-day bonding effectiveness

- of new self-etch adhesives to bur-cut enamel and dentin. *Oper Dent.* 2005; 30: 39-49.
- [26] Armstrong SR, Vargas MA, Fang Q, Laffoon JE. Microtensile bond strength of a total-etch 3-step, total-etch 2-step, self-etch 2-step, and a self-etch 1-step dentin bonding system through 15-month water storage. *J Adhes Dent.* 2003; 5: 47-56.
- [27] Goracci C, Sadek FT, Monticelli F, Cardoso PE, Ferrari M. Influence of substrate, shape, and thickness on microtensile specimens' structural integrity and their measured bond strengths. *Dent Mater.* 2004; 20: 643-654.
- [28] Poitevin A, De Munck J, Van Landuyt K, Coutinho E, Peumans M, Lambrechtse P, et al. Critical analysis of the influence of different parameters on the microtensile bond strength of adhesives to dentin. *J Adhes Dent.* 2008;10: 7-16.
- [29] Pashley DH, Sano H, Ciucchi B, Yoshiyama M, Carvalho RM. Adhesion testing of dentin bonding agents: a review. *Dent Mater.* 1995; 11: 117-125.
- [30] Gallusi G, Galeano P, Libonati A, Giuca MR, Campanella V. Evaluation of bond strength of different adhesive systems: Shear and Microtensile Bond Strength Test. *Oral Implantol (Rome).* 2009; 2: 19.
- [31] Takimoto M, Ishii R, Iino M, Shimizu Y, Tsujimoto A, Takamizawa T, et al. Influence of temporary cement contamination on the surface free energy and dentine bond strength of self-adhesive cements. *J Dent.* 2012; 40: 131-138.
- [32] Ribeiro JC, Coelho PG, Janal MN, Silva NR, Monteiro AJ, Fernandes CA. The influence of temporary cements on dental adhesive systems for luting cementation. *J Dent.* 2011; 39: 255-262.
- [33] Brigagão VC, Barreto LF, Gonçalves KA, Amaral M, Vitti RP, Neves AC, et al. Effect of interim cement application on bond strength between resin cements and dentin: Immediate and delayed dentin sealing. *J Prosthet Dent.* 2017; 117: 792-798.
- [34] Papacchini F, Dall Oca S, Chieffi N, Goracci C, Sadek FT, Suh BI, et al. Composite-to-composite microtensile bond strength in the repair of a microfilled hybrid resin: effect of surface treatment and oxygen inhibition. *J Adhes Dent.* 2007; 9: 25.
- [35] Pamato S, do Valle AL. Does hybridized dentin affect bond strength of self-adhesive resin cement? *J Clin Exp Dent.* 2016; 8: e409.
- [36] Seemann R, Flury S, Pfefferkorn F, Lussi A, Noack MJ. Restorative dentistry and restorative materials over the next 20 years: a Delphi survey. *Dent Mater.* 2014; 30: 442-448.
- [37] Dietschi D, Monasevic M, Krejci I, Davidson C. Marginal and internal adaptation of class II restorations after immediate or delayed composite placement. *J Dent.* 2002; 30: 259-269.
- [38] Irie M, Suzuki K, Watts D. Marginal gap formation of light-activated restorative materials: effects of immediate setting shrinkage and bond strength. *Dent Mater.* 2002; 18: 203-210.
- [39] Cardenas AM, Siqueira F, Hass V, Malaquias P, Gutierrez MF, Reis A, et al. Effect of MDP-containing silane and adhesive used alone or in combination on the long-term bond strength and chemical interaction with lithium disilicate ceramics. *J Adhes Dent.* 2017; 19: 203-212.
- [40] Pott PC, Stiesch M, Eisenburger M. Influence of 10-MD-P adhesive system on shear bond strength of zirconia-composite interfaces. *Clin Oral Implants Res.* 2015; 4: 117-126.
- [41] Ito S, Hashimoto M, Wadgaonkar B, Svizero N, Carvalho RM, Yiu C, et al. Effects of resin hydrophilicity on water sorption and changes in modulus of elasticity. *Biomaterials.* 2005; 26: 6449-6459.
- [42] Magne P. IDS: Immediate Dentin Sealing (IDS) for tooth preparations. *J Adhes Dent.* 2014; 16: 594.
- [43] Malysa A, Wezgowiec J, Orzeszek S, Florjanski W, Zietek M, Wieckiewicz M. Effect of different surface treatment methods on bond strength of dental ceramics to dental hard tissues: A systematic review. *Molecules.* 2021; 26: 1223.
- [44] Bona AD, Borba M, Benetti P, Cecchetti D. Effect of surface treatments on the bond strength of a zirconia-reinforced ceramic to composite resin. *Braz Oral Res.* 2007; 21: 10-15.
- [45] Magne P, Douglas WH. Rationalization of esthetic restorative dentistry based on biomimetics. *J Esthet Rest Dent.* 1999; 11: 5-15.
- [46] Magne P, Douglas WH. Porcelain veneers: Dentin bonding optimization and biomimetic recovery of the crown. *Int J Prosthodont.* 1999; 12: 111-121.
- [47] Rueggeberg F, Margeson D. The effect of oxygen inhibition on an unfilled/filled composite system. *J Dent Res.* 1990; 69: 1652-1658.
- [48] Khakiani MI, Kumar V, Pandya HV, Nathani TI, Verma P, Bhanushali NV. Effect of immediate dentin sealing on

- polymerization of elastomeric materials: an *ex vivo* randomized controlled trial. *Int J Clin Pediatr Dent.* 2019; 12: 288.
- [49] Leesungbok R, Lee SM, Park SJ, Lee SW, Lee DY, Im BJ, et al. The effect of IDS (immediate dentin sealing) on dentin bond strength under various thermocycling periods. *J Adv Prosthodont.* 2015; 7: 224-232.
- [50] Elbishari H, Elsubeihi ES, Alkhoujah T, Elsubeihi HE. Substantial *in vitro* and emerging clinical evidence supporting immediate dentin sealing. *Jpn Dent Sci Rev.* 2021; 57: 101-110.
- [51] Magne P, Nielsen B. Interactions between impression materials and immediate dentin sealing. *J Prosthet Dent.* 2009; 102: 298-305.
- [52] Gresnigt MM, Cune MS, Schuitemaker J, van der Made SA, Meisberger EW, Magne P, et al. Performance of ceramic laminate veneers with immediate dentine sealing: An 11 year prospective clinical trial. *Dent Mater.* 2019; 35: 1042-1052.
- [53] Van den Breemer CR, Buijs GJ, Cune MS, Özcan M, Kerdijk W, Van der Made S, et al. Prospective clinical evaluation of 765 partial glass-ceramic posterior restorations luted using photo-polymerized resin composite in conjunction with immediate dentin sealing. *Clin Oral Investig.* 2021; 25: 1463-1473.